

Copolymers of Pyrrole and α,ω -Dithienyl Terminated Poly(ethylene glycol)

Nesrin Köken, Esin A. Güvel, Nilgün Kızılcın

Abstract—This work presents synthesis of α,ω -dithienyl terminated poly(ethylene glycol) (PEGTh) capable for further chain extension by either chemical or electrochemical polymerization. PEGTh was characterized by FTIR and $^1\text{H-NMR}$. Further copolymerization of PEGTh and pyrrole (Py) was performed by chemical oxidative polymerization using ceric (IV) salt as an oxidant (PPy-PEGTh). PEG without end group modification was used directly to prepare copolymers with Py by Ce (IV) salt (PPy-PEG). Block copolymers with mole ratio of pyrrole to PEGTh (PEG) 50:1 and 10:1 were synthesized. The electrical conductivities of copolymers PPy-PEGTh and PPy-PEG were determined by four point probe technique. Influence of the synthetic route and content of the insulating segment on conductivity and yield of the copolymers were investigated.

Keywords—Chemical oxidative polymerization, conducting copolymer, poly(ethylene glycol), polypyrrole.

I. INTRODUCTION

THE unique properties of conducting polymers have brought these materials to forefront in miscellaneous applications such as electrochromic devices [1], energy storage systems [2], [3], sensors [4]-[6], catalysts [7], [8], actuators [9], electromagnetic interference shielding [10], textiles [11] and anticorrosive coatings [12]-[14]. Emerging developments in such specific fields have promoted scientists searching for advanced materials capable to achieve expected performance. Since preparation method gives opportunity to tailor conducting polymers they have been widely used to design novel materials with improved features. Several approaches to synthesis and modification of conducting polymers have been proposed. Side-chain introduced monomers [15], bulky dopants [16], [17], polymeric stabilizers [18], templates [19]-[21] and nanofillers [6], [22] have been used to prepare homopolymers, copolymers or composites of conducting polymers. It has been concurred that character of final product depends on a synthetic route and reaction conditions. Besides process may result in product with diverse physical forms (powders, films, nanoparticles, nanofibers, colloids and so forth).

Among the conducting polymers polypyrrole (PPy) is one

of the most intensively studied. (PPy)s synthesized by chemical oxidative, electrochemical, enzyme-catalized [23], [24], photo-induced [25], [26] and vapor phase [27], [28] polymerization methods have been reported. Copolymers, composites or blends of PPy and insulating polymers have been produced in order to obtain significant changes in electrical, mechanical, thermal and morphological properties of pristine conducting polymer.

Composites of pyrrole with insulating polymers are acrylic polymers [29]-[34], cellulose [35]-[37], polystyrene [38]-[42], polyurethane [43], polydimethylsiloxanes [44], [45], poly(ethylene glycol) [18], [46]-[54]. PEG is an inexpensive surfactant-like polymer with good solubility in most common solvents and can be easily reached commercially with wide range of molecular weights. Sterically stabilized colloids of polypyrrole were prepared using PEG as a stabilizer [18]. These conducting polymer colloids are two component systems, consisting of an inner core of conducting polymer surrounded by an outer layer of adsorbed, solvated, electrically insulating polymeric stabilizer. Upon solvent removal this stabilizer collapses down and coats the conducting polymer core forming an outer layer of negligible thickness. The results showed that such systems can significantly improve the processability of the electroactive component whilst retaining usefully high electrical conductivity, $2 \times 10^{-3} \text{ S.cm}^{-1}$. Lim and coworkers have reported soluble polypyrrole composites advanced in electrical conductivity. The composites were synthesized chemically with ammonium persulfate as an oxidant, dodecyl benzene sulfonate (DBS) sodium salt as a dopant, and PEG as an additive [53]. The PPy-DBS-PEG samples were found to be soluble in organic solvents such as N-methylpyrrolidinone and m-cresol. The solubility of the PPy-DBS-PEG samples increased when the molar percentage ratio of DBS was higher. The maximum electrical conductivity at room temperature for PPy-DBS-PEG was 1.02 S.cm^{-1} , in the case of mole % ratio of PPy:DBS:PEG was 100:10:40. Eisazadeh prepared polypyrrole and PEG composites chemically using FeCl_3 as an oxidant in aqueous and non-aqueous media. Results showed that conductivity is dependent on additive and type of solvent [49]. Solvents with more polar character (e.g. water) lead to polymers with higher conductivities since becomes more compatible with pyrrole. The conductivity decreases in non-aqueous media due to increase stabilizer adsorption, but as a result of an increase in the polymerization rate in the polar organic media, polydispersed particles are formed. PEG is stabilizing agents and could affect the size, morphology and the homogeneity of particles, because the surfactants are

N. Köken, is with the Department of Chemistry, Faculty of Science, Istanbul Technical University, 34469 Istanbul, Turkey. (corresponding author to provide phone: +90-212-285-285-7123; e-mail: nesrin@itu.edu.tr).

E. A. Güvel, is with the Department of Chemistry, Faculty of Science, Istanbul Technical University, 34469 Istanbul, Turkey. (phone: +90-535-641-2858; e-mail: esinatess@gmail.com).

N. Kızılcın, is with the Department of Chemistry, Faculty of Science, Istanbul Technical University, 34469 Istanbul, Turkey. (phone: +90-212-285-3242; e-mail: kizilcan@itu.edu.tr).

adsorbed physically to the polymer by the growing polymer. The PPy-PEG composite nanofibers were fabricated by electrospinning a solution of PEG and FeCl₃ in a water/ethanol solvent, followed by exposure to pyrrole vapors at ambient conditions [50]. PPy-PEG composite films were synthesized by electrochemical method, using *p*-toluene sulfonate as a dopant [48]. Both the electrical conductivity and thermal diffusivity exhibited the highest values with the process condition of 0.2 M pyrrole, 0.1 M *p*-toluene sulfonate and 1x10⁻³ M PEG at 1.2 V (versus SCE). α -Methoxy ω -Na carboxylate poly(ethylene glycol) has been synthesized and used as a bulky dopant for the electrochemical synthesis of polypyrrole films. The ion exchange properties of the formed composite have been analyzed in aqueous solution containing various salts [51]. The surface properties of electrodeposited PPy doped with sodium dodecylbenzenesulphonate are modified by two methods: addition of PEG during the electrodeposition and through redox cycling post electrodeposition [52]. Posudievsky et al. prepared a nanocomposite based on vanadium oxide and polypyrrole (PPy) and polyethylene glycol (PEG) by solventless mechanochemical synthesis. The composite containing two polymers with different types of conductivity (ionic and electronic) was chosen to obtain cathode material for lithium batteries [54].

Copolymer synthesis is another strategy used for modification of conducting polymers. Mainly chemical and electrochemical polymerization methods have been performed. Brittle, insoluble and infusible structure of conducting polymers, can be partially solved by preparing block copolymers prepared with a conducting polymer segment and a low-T_g polymer segment. This approach is most successful with systems like poly(3-hexylthiophene), where the conducting polymer can be functionalized to provide end groups suitable for block extension. Segmented copolymers containing PPy are most often prepared by end-capping the low-T_g block with a pyrrole or thiophene unit that can be chain extended via chemical or electrochemical polymerization, resulting in block and graft copolymers with moderate conductivities (10⁻² S.cm⁻¹) [55]. The studies related to synthesis of PPy based copolymers prepared with either PEG or end-capped PEG have been reported [55]-[57]. Luebben et. al have reported chemically synthesized copolymers of pyrrole and thiophene/pyrrole terminated insulating polymers, poly(ethylenedioxythiophene), poly(propylene glycol), poly(ethylene glycol), etc. [55]. Yildiz et al. have obtained electrochemically copolymer films of PEGTh and thiophene or pyrrole [56]. Gabriel et al. produced α -pyrrolyl- ω -acrylate-poly(ethylene glycol) as a dual macromonomer and prepared electrochemically copolymers in the mixture of pyrrole and α -pyrrolyl- ω -hydroxy-poly(ethylene glycol) [57].

The present work deals with the synthesis of block copolymers of pyrrole and α,ω -dithienyl terminated poly(ethylene glycol). The copolymers were synthesized by chemical oxidative polymerization in aqueous medium using cerium(IV) ammonium nitrate (CAN) as an oxidant and *p*-

toluene sulfonic acid (PTSA) as a dopant. Two different mole ratios of pyrrole to PEGTh was applied, 50:1 and 10:1. Since cerium(IV) salt is capable to oxidize both Py and hydroxymethyl groups of PEG, alternative copolymerization route was performed as a comparative study. The electrical conductivities were measured via 4-point probe technique. Influence of synthetic route and ratio of conducting to insulating segment on conductivities and yield of the copolymers were demonstrated.

II. MATERIALS AND METHODS

Pyrrole, poly(ethylene glycol) (Mn=1000), ammonium cerium(IV) nitrate, and 2-thiophenecarbonyl chloride (Sigma-Aldrich), *p*-toluenesulfonic acid monohydrate and pyridine (Acros Organics) were purchased with analytical grade and were used without any purification.

Infrared spectra were recorded on an FTS-6000 Excalibur FTIR, using Varian Resolutions Pro as software. ¹H-NMR measurements were performed on Varian Mercury 400 spectrometer at room temperature, using CDCl₃ as deuterated solvent. Electrical conductivities (σ) of polymers were determined by four point probe technique using Keithley 2400 model multimeter, Lucas Labs 302 model probe holder and SP4-180-TFS type probe. Thin pellets with typical sample diameter of 13 mm were prepared by compaction of the polymer powders under 10 tons of pressure. Conductivities were calculated from the following equation:

$$\sigma = V^{-1} \cdot I (\ln 2 / \pi d n) \quad (1)$$

where V is the potential in volts, I is the current in ampere and dn is the thickness of the samples in cm.

Morphologies of products were examined by scanning electron microscope, ESEM XL30 ESEM-FEG Philips.

III. EXPERIMENTAL

A. Synthesis of Polypyrrole with Ceric(IV) Salt in Aqueous Medium

0.3 ml (4.3 mmol) pyrrole and 2.53 g (13 mmol) PTSA were added into 45 ml of water and stirred. Calculated amount of cerium(IV) ammonium nitrate (CAN) was dissolved in 10 ml of water. Then prepared solution of ceric(IV) salt was added dropwise. Reaction was maintained for 1 hour at room temperature. Precipitated PPy was filtered off and washed with water, methanol and acetone. Polymer was dried at 45 °C for 24 hours. (PPy)s were prepared using n(CAN):n(Py) mole ratio of 0.25, 0.33, 0.5 and 1.0. The set of experiments were carried out without PTSA.

B. Synthesis of α,ω -Dithienyl Terminated Poly(Ethylene Glycol)

10 g (10 mmol) poly(ethylene glycol) (Mn:1000) was dissolved in 40 ml dry chloroform inside the three-necked flask equipped with dropping funnel and cooler. Then 1.77 ml (22 mmol) pyridine was added and the mixture was stirred under argon atmosphere. The system was placed in an ice-

methods, FTIR and $^1\text{H-NMR}$ (Figs. 4 and 5).

Infrared spectra of PEG and PEGTh were compared in Fig 4.

The spectra mainly differ from each other by additional absorption bands appeared in the spectrum of PEGTh. The bands coming from the thiophene moiety were observed at 3089 cm^{-1} and 1707 cm^{-1} corresponding to aromatic C-H and C=O stretching vibrations, respectively.

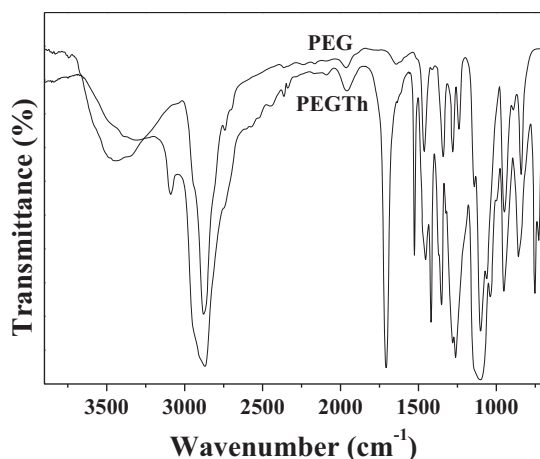


Fig. 4 FTIR spectra of PEG and PEGTh

Fig. 5 represents $^1\text{H-NMR}$ spectra of 2-thiophenecarbonyl chloride, poly(ethylene glycol) and α,ω -dithienyl terminated poly(ethylene glycol). In the spectrum of ThCCl aromatic protons of thiophene ring showed signals at 7.99-7.83-7.20 ppm. In the case of PEGTh these signals shifted to 7.80-7.57-7.10 ppm, respectively. The signal appeared at 4.43 ppm is related to aliphatic protons adjacent to the ester group.

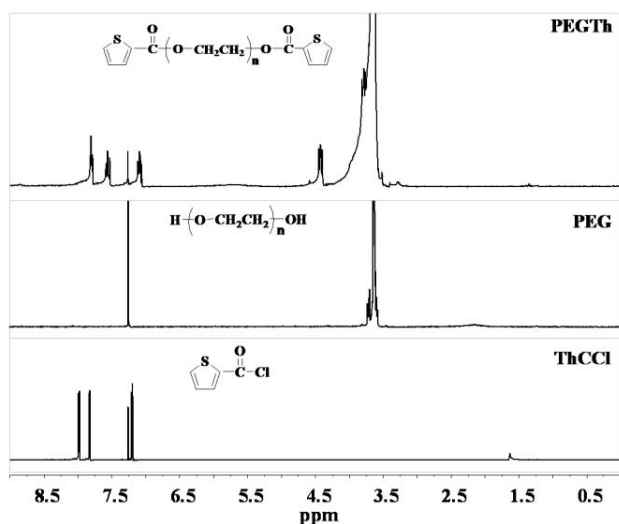


Fig. 5 $^1\text{H-NMR}$ spectra of PEG and PEGTh in CDCl_3

The chemical structure of copolymers were determined by means of FTIR. Products were found to have similar absorption bands. The spectrum of PPy-PEGTh copolymer is shown in Fig. 6. Aromatic and aliphatic protons showed bands

at 3107 cm^{-1} and $2900\text{-}2800\text{ cm}^{-1}$, respectively. The absorption band related to C=O stretching vibrations shifted and appeared at 1694 cm^{-1} . Signals observed at $1580\text{-}1520\text{ cm}^{-1}$ belong to aromatic C=C stretching, and signals obtained at $1300\text{-}1000\text{ cm}^{-1}$ belong to C-N and C-O stretching vibrations.

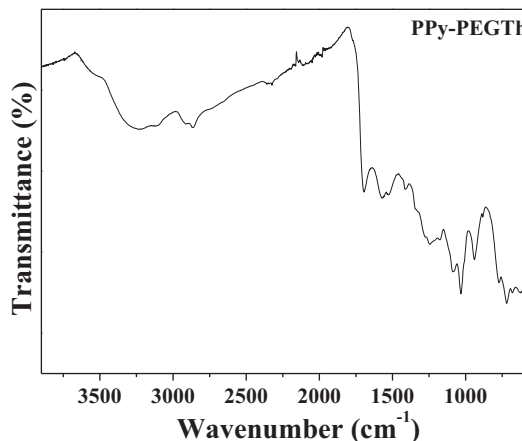


Fig. 6 FTIR spectrum of PPy-PEGTh

Synthesis of copolymers via chemical oxidative polymerization and proposed structure of copolymers was introduced in Figs. 7 and 8.

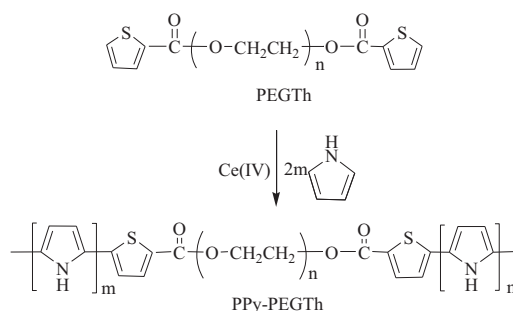


Fig. 7 Synthesis of PPy-PEGTh copolymer

Fig. 7 represents synthesis of pyrrole and α,ω -dithienyl terminated poly(ethylene glycol) using cerium(IV) ammonium nitrate.

Fig. 8 represents synthesis of pyrrole and poly(ethylene glycol) using cerium(IV) ammonium nitrate.


TABLE I
CONDUCTIVITY AND YIELD DATA FOR POLYMERS

Polymer	[CAN]	[PTSA]	[Py]	[PEG] or [PEGTh]	Yield (%)	σ (S.cm^{-1})
PPy	0.039	0.24	0.078	-	33	0.09
PPy-PEG1	0.039	0.24	0.078	0.0016	25	0.14
PPy-PEGTh1	0.039	0.24	0.078	0.0016	26	0.28
PPy-PEG2	0.039	0.24	0.078	0.0078	15	0.74
PPy-PEGTh2	0.039	0.24	0.078	0.0078	13	0.63

In Table I results were compared in the terms of conductivity and percentage of yield. The copolymers have conductivities in the range of 0.14 S.cm^{-1} - 0.74 S.cm^{-1} . Increase in concentration of PEGTh (PEG) caused decrease in yield

and increase in conductivity of copolymers.

Initiation

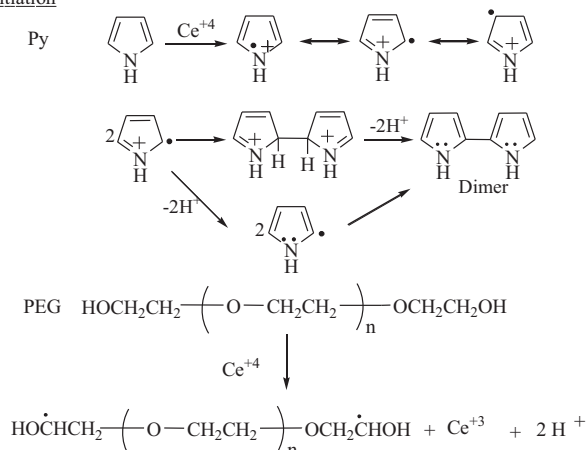

Propagation and Termination

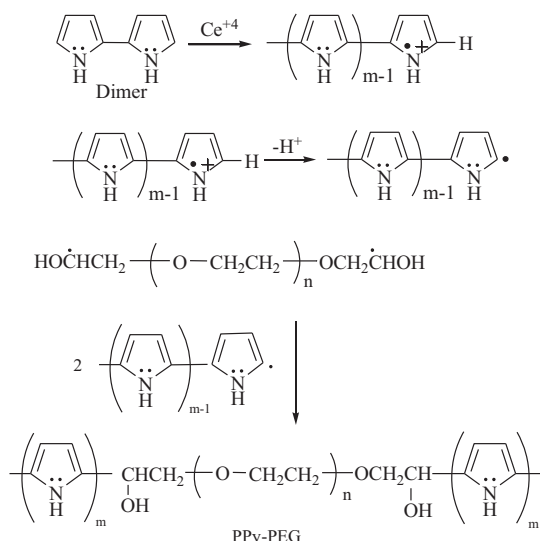


Fig. 8 Synthesis of PPy-PEG copolymer

Morphologies of PPy-PEGTh2 and PPy samples were compared in Figs. 9 and 10. Surface of polypyrrole was found to be more compact and denser than copolymer.

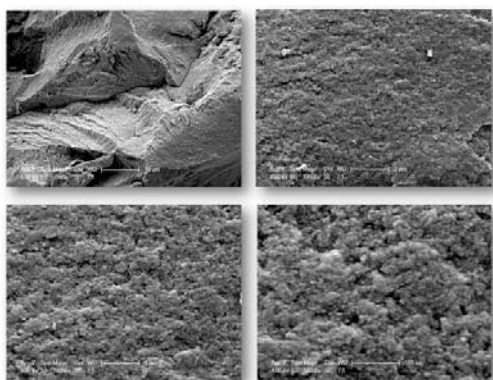


Fig. 9 SEM micrographs of PPy

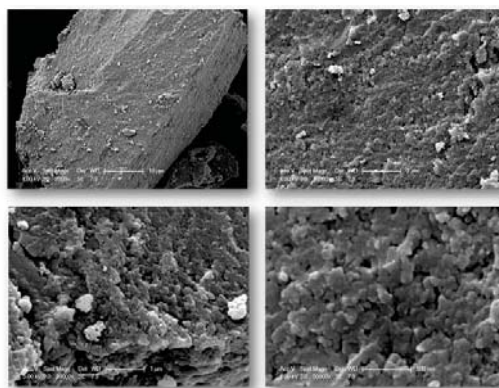


Fig. 10 SEM micrographs of PPy-PEGTh2

REFERENCES

- [1] S. Ahmad, S. S. Gursory, S. Kazim, A. Uygun, "Growth of N-substituted polypyrrole layers in ionic liquids: Synthesis and its electrochromic properties", *Solar Energy Materials & Solar Cells*, vol. 99, pp. 95–100, 2012.
- [2] J. F. Mike, J. L. Lutkenhaus, "Recent advances in conjugated polymer energy storage", *Journal of Polymer Science, Part B: Polymer Physics*, vol. 51, pp. 468–480, 2013.
- [3] R. Holze and Y. P. Wu, "Intrinsically conducting polymers in electrochemical energy technology: Trends and progress", *Electrochimica Acta*, vol. 122, pp. 93–107, 2014.
- [4] P. S. Sharma, A. Pietrzyk-Le, F. D'Souza, W. Kutner, "Electrochemically synthesized polymers in molecular imprinting for chemical sensing", *Anal. Bioanal. Chem.*, 402:3177–3204, 2012.
- [5] S. T. Navale, A. T. Mane, M. A. Chougule, R. D. Sakhare, S. R. Nalage, V. B. Patil, "Highly selective and sensitive room temperature NO₂ gas sensor based on polypyrrole thin films", *Synthetic Metals*, vol. 189, pp. 94–99, 2014.
- [6] J. Li, H. Xie and Y. Li, "Fabrication of gold nanoparticles/polypyrrole composite-modified electrode for sensitive hydroxylamine sensor design", *J. Solid State Electrochem.*, vol. 16, pp. 795–802, 2012.
- [7] X. Liang, Y. Cheng and C. Qi, Polypyrrole based strong acid catalyst for acetalization, *Solid State Sciences*, vol. 13, pp. 1820–1824, 2011.
- [8] J. Wang, J. Wang, Z. Wang and S. Wang, "Electrocatalytic oxidation of ascorbic acid at polypyrrole nanowire modified electrode", *Synthetic Metals*, vol. 156, pp. 610–613, 2006.
- [9] W. Zheng, G. Alici, P. R. Clingan, B. J. Munro, G. M. Spinks, J. R. Steele, G. G. Wallace, "Polypyrrole stretchable actuators", *Journal of Polymer Science Part B: Polymer Physics*, vol. 51, pp. 57–63, 2013.
- [10] Y. Wang and X. Jing, "Intrinsically conducting polymers for electromagnetic interference shielding", *Polym. Adv. Technol.*, vol. 16, pp. 344–351, 2005.
- [11] D. Das, K. Sen and S. Maity, "Studies on electro-conductive fabrics prepared by in situ chemical polymerization of mixtures of pyrrole and thiophene onto polyester", *Fibers and Polymers*, vol.14, (3), pp. 345–351, 2013.
- [12] P. Zarras, N. Anderson, C. Webber, D. J. Irvin, J. A. Irvin, A. Guenther and J. D. Stenger-Smith, "Progress in using conductive polymers as corrosion-inhibiting coatings", *Radiation Physics and Chemistry*, vol. 68, pp. 387–394, 2003.
- [13] M. I. Khan, A. U. Chaudhry, S. Hashim, M. K. Zahoor and M. Z. Iqbal, "Recent developments in intrinsically conductive polymer coatings for corrosion protection", *Chemical Engineering Research Bulletin*, vol. 14, pp. 73–86, 2010.
- [14] M. Shabani-Nooshabadi, S. M. Ghoreishi, Y. Jafari and N. Kashanizadeh, "Electrodeposition of polyaniline-montmorillonite nanocomposite coatings on 316L stainless steel for corrosion prevention", *Journal of Polymer Research*, vol. 21: 416, 2014.
- [15] W. M. Sigmund, G. Weerasekera, C. Marestin, S. Styron, H. Zhou, M. Z. Elsabee, J. R uhe, G. Wegner, and R. S. Duran, "Polymerization of monolayers of 3-substituted pyrroles", *Langmuir*, vol. 15, pp. 6423–6427, 1999.
- [16] J. Stejskal, M. Omastova, S. Fedorova, J. Prokeš, and M. Trchova, "Polyaniline and polypyrrole prepared in the presence of surfactants: a

- comparative conductivity study”, *Polymer*, vol. 44, pp. 1353–1358, 2003.
- [17] A. Kaynak, L. Rintoul and G. A. George, “Change of mechanical and electrical properties of polypyrrole films with dopant concentration and oxidative aging”, *Materials Research Bulletin*, vol. 35, pp. 813–824, 2000.
- [18] S. P. Armes, M. Aldissi, G. C. Idzorek, P. W. Keaton, L. J. Rowton, G. L. Stradling, M. T. Collopy, and D. B. McColl, “Particle size distributions of polypyrrole colloids”, *Journal of Colloid and Interface Science*, vol. 141 (1), pp. 119–126, 1991.
- [19] X. Li, X. Zhang and Li, H., “Preparation and characterization of pyrrole/aniline copolymer nanofibrils using the template–synthesis method”, *Journal of Applied Polymer Science*, vol. 81, pp. 3002–3007, 2001.
- [20] X. Li, M. Lu and Li H., “Electrochemical copolymerization of pyrrole and thiophene nanofibrils using template–synthesis method”, *Journal of Applied Polymer Science*, vol. 86, pp. 2403–2407, 2002.
- [21] N. Li, D. Shan and H. Xue, “Electrochemical synthesis and characterization of poly(pyrrole–co–tetrahydrofuran) conducting copolymer”, *European Polymer Journal*, vol. 43, pp. 2532–2539, 2007.
- [22] N. Ballav and M. Biswas, “A conducting nanocomposite via intercalative polymerisation of thiophene in montmorillonite clay”, *Synthetic Metals*, vol. 142, pp. 309–315, 2004.
- [23] H. K. Song and G. T. R. Palmore, “Conductive polypyrrole via enzyme catalysis”, *J. Phys. Chem. B*, vol. 109, pp. 19278–19287, 2005.
- [24] A. Ramanaviciene, W. Schuhmann and A. Ramanavicius, “AFM study of conducting polymer polypyrrole nanoparticles formed by redox enzyme–glucose oxidase–initiated polymerization”, *Colloids and Surfaces B: Biointerfaces*, vol. 4, pp. 159–166, 2006.
- [25] K. Kijewska, G. J. Blanchard, J. Szlachetko, J. Stolarski, A. Kisiel, A. Michalska, K. Maksymiuk, M. Pisarek, P. Majewski, P. Kryszinski and M. Mazur, “Photopolymerized polypyrrole microvessels”, *Chem. Eur. J.*, vol. 18, pp. 310–320, 2012.
- [26] H. R. Heydamezhad and B. Pourabbas, “One–step synthesis of conductive ceria/polypyrrole nanocomposite particles via photo–induced polymerization method”, *J. Mater. Sci.: Mater. Electron.*, vol. 24, pp. 4378–4385, 2013.
- [27] A. T. Lawal and G. G. Wallace, “Vapour phase polymerisation of conducting and non–conducting polymers: A review”, *Talanta*, vol. 119, pp. 133–143, 2014.
- [28] D. Bhattacharyya, R. M. Howden, D. C. Borrelli and K. K. Gleason, “Vapor phase oxidative synthesis of conjugated polymers and applications”, *Journal of Polymer Science Part B: Polymer Physics*, vol. 50, pp. 1329–1351, 2012.
- [29] M. Omastová and F. Simon, “Surface characterizations of conductive poly(methyl methacrylate)/polypyrrole composites”, *Journal of Materials Science*, vol. 35, pp. 1743–1749, 2000.
- [30] H. Acar, M. Karakışla and M. Saçak, “Potassium persulfate-mediated preparation of conducting polypyrrole/polyacrylonitrile composite fibers: Humidity and temperature-sensing properties”, *Journal of Applied Polymer Science*, vol. 125, pp. 3977–3985, 2012.
- [31] C. Unsal, F. Kalaoglu, H. Karakas and A. S. Sarac, “Polypyrrole/poly(acrylonitrile–co–butyl acrylate) composite”, *Advances in Polymer Technology*, vol. 32 (S1), pp. E784–E792, 2013.
- [32] A. Shakoob, P. J. S. Foot and T. Z. Rizvi, “Conductive poly(methyl methacrylate)–polypyrrole dodecylbenzenesulfonate (PMMA–PPy,DBSA) blends prepared in solution in the presence of hydroquinone”, *J. Mater. Sci.: Mater. Electron.*, vol. 21, pp. 1270–1276, 2010.
- [33] M. Ferenets and A. Harlin, “Chemical in situ polymerization of polypyrrole on poly(methyl methacrylate) substrate”, *Thin Solid Films*, vol. 515, pp. 5324–5328, 2007.
- [34] F. Huijs and J. Lang, “Morphology and film formation of poly(butyl methacrylate)–polypyrrole core–shell latex particles”, *Colloid Polym. Sci.*, vol. 278, pp. 746–756, 2000.
- [35] D. Zhang, Q. Zhang, X. Gao, and G. Piao, “A nanocellulose polypyrrole composite based on tunicate cellulose”, *International Journal of Polymer Science*, 2013, pp. 1–6, 2013.
- [36] J. Li, X.-R. Qian, J.-H. Chen, C.-Y. Ding, and X.-H. An, “Conductivity decay of cellulose–polypyrrole conductive paper composite prepared by in situ polymerization method”, *Carbohydrate Polymers*, 82, 504–509, 2010.
- [37] M. Mic’ušik, M. Omastová, J. Prokeš, and I. Krupa, “Mechanical and electrical properties of composites based on thermoplastic matrices and conductive cellulose fibers”, *Journal of Applied Polymer Science*, vol. 101, pp. 133–142, 2006.
- [38] S. Bousalem, C. Mangeney, Y. Alcote, M.M. Chehimi, T. Basinska and S. Slomkowski, “Immobilization of proteins onto novel, reactive polypyrrole–coated polystyrene latex particles”, *Colloids and Surfaces A: Physicochem. Eng. Aspects*, vol. 249, pp. 91–94, 2004.
- [39] X.-J. Xu, L.-M. Gan, K.-S. Siow and M.-K. Wong, “Synthesis and characterization of nanosized polypyrrole–polystyrene composite particles”, *Journal of Applied Polymer Science*, vol. 91, pp. 1360–1367, 2004.
- [40] J. M. Lee, D. G. Lee, S. J. Lee, and J. H. Kim, “One–step synthetic route for conducting core–shell poly(styrene/pyrrole) nanoparticles”, *Macromolecules*, vol. 42, pp. 4511–4519, 2009.
- [41] M. Han, K. Zhao, Y. Zhang, Z. Chen, and Y. Chu, Dielectric properties of polystyrene–polypyrrole core–shell conducting spheres suspended in aqueous solution, *Colloids and Surfaces A: Physicochem. Eng.*, vol. 302, pp. 174–180, 2007.
- [42] Z. Huang, C. Wang, Y. Li, and Z. Wang, “Controlled preparation of core–shell polystyrene/polypyrrole nanocomposite particles by a swelling–diffusion–interfacial polymerization method”, *Colloid Polym. Sci.*, vol. 290, pp. 979–985, 2012.
- [43] C. R. Broda, J. Y. Lee, S. Sirivisoot, C. E. Schmidt and B. S. Harrison, “A chemically polymerized electrically conducting composite of polypyrrole nanoparticles and polyurethane for tissue engineering”, *J. Biomed. Mater. Res. Part A*, 98A, 509–516, 2011.
- [44] G. Çakmak, Z. Küçükyavuz, and S. Küçükyavuz, “Flexible and conducting composites of polypyrrole and polydimethylsiloxane”, *Journal of Applied Polymer Science*, vol. 93, pp. 736–74, 2004.
- [45] W.-I. Son, J.-M. Hong, and B.-S. Kim, “Polypyrrole composite membrane with high permeability prepared by interfacial polymerization”, *Korean J. Chem. Eng.*, vol. 22 (2), pp. 285–290, 2005.
- [46] C. Pirvu, C. C. Manole, A. B. Stoian, I. Demetrescu, “Understanding of electrochemical and structural changes of polypyrrole/polyethylene glycol composite films in aqueous solution”, *Electrochimica Acta*, vol. 56, pp. 9893–9903, 2011.
- [47] Y.-C. Liu and B.-J. Hwang, “Enhancement of conductivity stability of polypyrrole films modified by valence copper and polyethylene oxide in an oxygen atmosphere”, *Thin Solid Films*, vol. 360, pp. 1–9, 2000.
- [48] L. M. Yee, H. N. M. E. Mahmud, A. Kassim, and W. M. M. Yunus, “Polypyrrole–polyethylene glycol conducting polymer composite films: Preparation and characterization” *Synthetic Metals*, vol. 157, pp. 386–389, 2007.
- [49] H. Eisazadeh, “Studying the characteristics of polypyrrole and its composites”, *World Journal of Chemistry*, vol. 2 (2), pp. 67–74, 2007.
- [50] S. Nair, S. Natarajan, and S. H. Kim, “Fabrication of electrically conducting polypyrrole–poly(ethylene oxide) composite nanofibers”, *Macromol. Rapid Commun.*, vol. 26, pp. 1599–1603, 2005.
- [51] C. Jérôme, L. Martinot and R. Jérôme, “Ion–exchange properties of polypyrrole doped by ω –carboxylated polyethyleneoxide”, *Synthetic Metals*, vol. 105, pp. 65–71, 1999.
- [52] K. M. Sivaraman, B. Özkale, O. Ergeneman, T. Lühmann, G. Fortunato, M. A. Zeeshan, B. J. Nelson and S. Pané, “Redox cycling for passive modification of polypyrrole surface properties: Effects on cell adhesion and proliferation”, *Adv. Healthcare Mater.*, vol. 2, pp. 591–598, 2013.
- [53] H. K. Lim, S. O. Lee, K. J. Song, S. G. Kim, and K. H. Kim, “Synthesis and properties of soluble polypyrrole doped with dodecylbenzenesulfonate and combined with polymeric additive poly(ethylene glycol)”, *Journal of Applied Polymer Science*, vol. 97, pp. 1170–1175, 2005.
- [54] O. Y. Posudievsky, O. A. Kozarenko, V. S. Dyadyun, S. W. Jorgensen, J. A. Spearot, V.G. Koshechko and V. D. Pokhodenko, “Mechanochemically prepared ternary hybrid cathode material for lithium batteries”, *Electrochimica Acta*, vol. 109, pp. 866–873, 2013.
- [55] S. D. V. Luebben, B. Elliott, and C. Wilson, “Poly(heteroaromatic) block copolymers with electrical conductivity”, *US Patent 7 279 534 B2*, 2007.
- [56] H. B. Yildiz, S. Kiralp, L. Toppare, Y. Yagci and K. Ito, “Synthesis of conducting copolymers of thiophene capped poly(ethylene oxide) with pyrrole and thiophene”, *Materials Chemistry and Physics*, vol. 100 (1), pp. 124–127, 2006.
- [57] S. Gabriel, M. Ce’cius, K. Fleury-Frenette, D. Cossement, M. Hecq, N. Ruth, R. Jérôme, and C. Jérôme, “Synthesis of adherent hydrophilic polypyrrole coatings onto (semi)conducting surfaces”, *Chem. Mater.*, vol. 19, pp. 2364–2371, 2007.



Nesrin Köken was born in Istanbul, Turkey, in 1967. She is currently a Lecturer and Researcher in the Organic Chemistry group in Chemistry Department, and Polymer Science and Technology Programmers at Istanbul Technical University. She obtained her BSc in Chemistry Department in 1989, her MSc and PhD degrees in chemistry at the same university in 1992 and 1997, respectively.

Köken has published 11 research papers and 13 national and 14 international presentations. She was 5 completed research project coordinators, 1 PhD thesis supervisors, 6 MSc thesis supervisors. She specializes in emulsion polymerization, conducting polymer and copolymers.

Assoc. Prof. Dr. Nesrin Köken is a member of Deutscher Akademischer Austausch Dienst German Academic Exchange Service (DAAD) and Turkish Chemical Society.



Esin Ateş Güvel was born in Razgrad, Bulgaria, in 1979. She is currently a doctoral student with the Chemistry Programme at Istanbul Technical University. She obtained her BSc degree in chemistry from Trakya University in 2002 and MSc degree in chemistry program at Istanbul Technical University 2005, respectively.

A. Güvel has published 4 research papers, 8 national and 4 international presentations.



Nilgün Kızılcan was born in İstanbul, Turkey, in 1965. She is currently a Lecturer and Researcher in the Organic Chemistry group in Chemistry Department and Polymer Science and Technology Programmers at Istanbul Technical University. She obtained her BSc in Chemical Engineering Department in 1986, her MSc and PhD degrees in chemistry at the same university in 1990 and 1995, respectively.

Kızılcan has published 44 research papers and 48 national and 47 international presentations. She was 16 completed research project coordinators, 5 PhD thesis supervisors, 18 MSc thesis supervisors. She wrote book chapters in 2 books. She is on the Editorial Advisory Board of ISRN Polymer Science. She specializes in resins, conducting polymer and copolymers.

Professor N. Kızılcan is a member of Turkish Chamber of Chemical Engineers.