

# The Adsorption of Zinc Metal in Waste Water Using ZnCl<sub>2</sub> Activated Pomegranate Peel

S. N. Turkmen, A. S. Kipcak, N. Tugrul, E. M. Derun, S. Piskin

**Abstract**—Activated carbon is an amorphous carbon chain which has extremely extended surface area. High surface area of activated carbon is due to the porous structure. Activated carbon, using a variety of materials such as coal and cellulosic materials; can be obtained by both physical and chemical methods. The prepared activated carbon can be used for decolorize, deodorize and also can be used for removal of organic and non-organic pollution. In this study, pomegranate peel was subjected to 800W microwave power for 1 to 4 minutes. Also fresh pomegranate peel was used for the reference material. Then ZnCl<sub>2</sub> was used for the chemical activation purpose. After the activation process, activated pomegranate peels were used for the adsorption of Zn metal (40 ppm) in the waste water. As a result of the adsorption experiments, removal of heavy metals ranged from 89% to 85%.

**Keywords**—Activated carbon, chemical activation, microwave, pomegranate peel.

## I. INTRODUCTION

THERE are effective method as adsorption which is relatively useful and economical for quickly lowering the concentration of pollutants such as organic compounds, metal ions and dissolved dyes in an effluent [1]. Because of their mechanical stability, low specificity, fast adsorption kinetics and high adsorption capacities, activated carbon is accepted as one of the most popular material for adsorption [2], [3].

Activated carbon which has great capacity of adsorbing for various organic compounds such as dyes, heavy metals, pharmaceutical and surfactants are the most commonly used adsorbent. But price of activated carbon is relatively high. For this reason initiative have been started to study reduced cost and made of natural sorbents to remove impurity from wastewater. About production of activated carbon using lower cost methods and materials from renewable resources have been searched by many researchers. In some of this research, activated carbon using agricultural and industrial waste materials was produced. [4]–[10]. Activated carbon can be produced from all carbon-containing lignocellulosic agricultural waste as lignin [11], macro-algal [12], defective coffee press cake [13], palm shell [14], rice husk [15] wastes of vegetable origin (e.g. nut shells and fruit stones) [16].

S. N. Turkmen, N. Tugrul, E. M. Derun, and S. Piskin are with the Yildiz Technical University, Department of Chemical Engineering, Davutpasa Campus, 34210 Esenler, Istanbul, Turkey (e-mail: seymaturkmen@gmail.com, ntugrul@yildiz.edu.tr, moroydor@yildiz.edu.tr, piskin@yildiz.edu.tr).

A. S. Kipcak is with the Yildiz Technical University, Department of Chemical Engineering, Davutpasa Campus, 34210 Esenler, Istanbul, Turkey (phone: 0090-212-3834758; fax: 0090-212-3834725; e-mail: skipcak@yildiz.edu.tr).

Solid waste of peel/skin, stones or seeds obtained from processing of fruits can be used production of activated carbon. One of these fruits is pomegranate (*Punica granatum* L.) and the total production of pomegranate in the world is about 1 million tonnes [17]. Turkey which the annual production of pomegranate in is about 60,000 tons is one of the world's largest producers [18].

Activated carbons are produced by physical or chemical activation. Chemical activation can be carried out by thermal decomposition of raw material with chemical reagents. Chemicals as zinc chloride (ZnCl<sub>2</sub>), phosphoric acid (H<sub>3</sub>PO<sub>4</sub>), and potassium hydroxide/carbonate (KOH/K<sub>2</sub>CO<sub>3</sub>) is used commonly. An example of chemical activation with ZnCl<sub>2</sub> is that Olivares-Marin et al. prepared activated carbon from cherry stones [19]. In another study, Angin et al. produced activated carbons were from biochar of safflower seed press cake by chemical activation with ZnCl<sub>2</sub>. It was reported that activation temperature and impregnation ratios are more influence on the porosity, surface area and adsorption capacity of activated carbons [20].

As the investigations, used microwave process instead of pyrolysis [21]-[23] provide lots of advantage as high heating rates, controllable and selective heating; energy and time savings [24].

In this study, pomegranate peel was subjected to pretreatment with microwave power for different times. As the reference material fresh pomegranate peel was used. Activated carbons were prepared by chemical activation with ZnCl<sub>2</sub> of the biochar obtained through microwave of pomegranate peel. After the activation process, adsorption capacities of the activated carbons were investigated.

## II. EXPERIMENTAL METHOD

Pomegranate peels (Fig. 1) were collected from local juice bar. The residual dreg after juicing process is separated from pomegranate peel. Then pomegranate peel was washed with tap water to remove dusts and dried over night at 70°C. It was granulated and then sieved through a 20 mesh sieve. Dry pomegranate peel powder was stored in food storage bag at room temperature. Pomegranate peel powder is shown in Fig. 2.

The MW treatment was carried out using a Robert Bosch HMT72G420 Microwave Oven (Fig. 3). Sample was exposed to a maximum power of 800 W with an operating microwave frequency of 2.45 GHz (wavelength 12.2 cm).

A gram of sample of dry pomegranate peel was placed in each of watch glass. Two watch glasses so as to opposite with each other were placed in microwave oven. Microwave oven was started under constant MW power (800 W) and air

atmosphere. Process was carried out for 1 to 4 minutes.

Samples which had exposed to microwave, were added into  $ZnCl_2$  solution (weight ratio=1:3) and stirred at 500 rpm. This process is shown in Fig. 4. After 2 h, mixture was decanted and then solid phase was added to HCl. After 1 h stirring, rinsed with deionized distilled water several times until pH 5.5. Product was dried over night at  $105^\circ C$ . Dry pomegranate peels without microwave pretreatment was implemented same chemical activation. It was used as a reference material.



Fig. 1 Pomegranate peel



Fig. 2 Pomegranate peel powder



Fig. 3 Robert Bosch HMT72G420 Microwave Oven

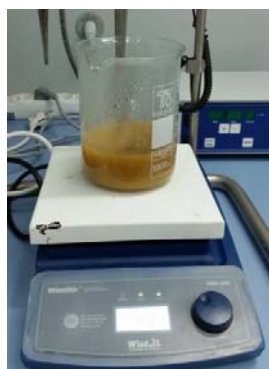


Fig. 4 Mixture of sample and  $ZnCl_2$



Fig. 5 Perkin Elmer Spectrum One FT-IR

Then samples were characterized with Perkin Elmer Spectrum One Fourier Transform Infrared Spectroscopy (FT-IR), (Fig. 5) with Universal ATR sampling accessory – Diamond / ZnSe Crystal. Working region of FTIR spectra was selected between  $1800$  and  $650\text{ cm}^{-1}$ .

For the adsorption process (Fig. 6),  $0.25\text{g}$  of the activated carbon products was mixed with  $40\text{ ppm}$  of Zn solutions ( $50\text{ ml}$ ). The mixture was stirred at  $500\text{rpm}$  for  $2\text{h}$  at room temperature ( $22\pm 0.5\text{ }^\circ C$ ). Zn solution and activated carbon was separated from each other by using filter paper. The equilibrium concentrations of Zn were measured by using Perkin Elmer 35 Lambda UV/Vis Spectrophotometer (Fig. 7) at wavelength  $300\text{ nm}$ .



Fig. 6 Adsorption process



Fig. 7 Perkin Elmer 35 Lambda UV/Vis Spectrophotometer

### III. RESULTS AND DISCUSSION

#### A. Results of Microwave Pre-Treated Samples

After microwave process, results of loss weight of samples shown in Table I.

Time of Microwave	Weight Loss (%)
1	8
2	17
3	23
4	28

Synthesized Activated Carbon	Remaining Zn (II) in Solution (ppm)
Reference material	6.06
1	5.73
2	5.34
3	5.31
4	4.63

As a result, weight loss of the samples increased with increasing time. This situation may be due to volatilization of certain volatile component.

### B. Characterizations of the Activated Carbons

FT-IR spectra of prepared activated carbons and raw materials are shown in Fig. 8. In Fig. 8 the numbers at the right hand side represents the exposure time of samples in the microwave. Fig. 9 represents the FT-IR spectrum of commercial activated carbon.

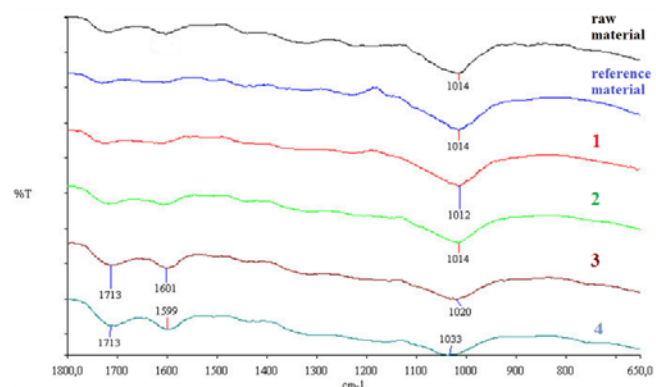


Fig. 8 FT-IR spectra of synthesized activated carbons and raw material

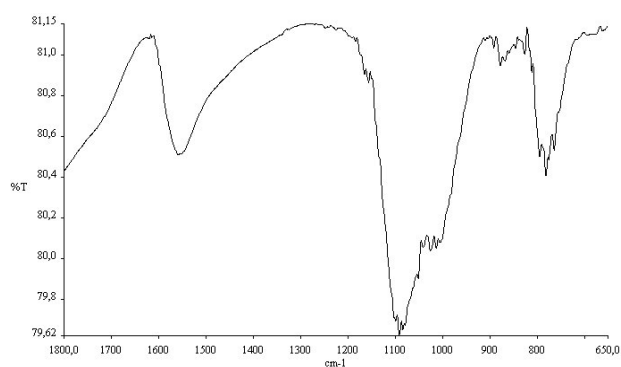


Fig. 9 FT-IR spectrum of commercial activated carbon

In all of spectra placed Figs. 8 and 9; vibration of C–O–C ( $1000\text{--}1100\text{ cm}^{-1}$ ) is observed. Different from the prepared activated carbon samples, in activated carbon, ester C=O ( $1713\text{ cm}^{-1}$ ) and aromatic C=C and C=O (about  $1600\text{ cm}^{-1}$ ) were seen.

### C. Results of Adsorption of Zn (II) by Activated Carbon

Adsorption of Zn (II) by activated carbons is presented in Table II.

From the results it is seen that the increase in the microwave exposure time leads to better adsorption of Zn (II).

## IV. CONCLUSIONS

Because of used activated carbon as most commonly adsorbent, investigation about reducing cost of activated carbon has been the major objective. For this reason, especially as alternative method and raw materials has been focused on a microwave energy and bio-waste. While microwave process has advantages like saving energy and time; bio-waste is low cost raw material.

In this study, the adsorption capacities of activated carbon obtained by exposure microwave energy at different times were investigated. When reference material is compared with activated carbons, the capacity of adsorption of Zn is increased with the increasing microwave exposure time.

In the future studies, activated carbon will be obtained by changing the sequence of process and ratio of chemical agents and raw materials.

## REFERENCES

- [1] V. K. Gupta and S. Suhas, "Application of low-cost adsorbents for dye removal—a review," *Journal of Environmental Management*, vol. 90, no. 8, pp. 2313–2342, 2009.
- [2] A. A. Halim, H. A. Aziz, M. A. M. Johari, K. S. Ariffin, Comparison study of ammonia and COD adsorption on zeolite, activated carbon and composite materials in landfill leachate treatment, *Desalination*, vol. 262, 31–35, 2010.
- [3] S.L Wang, Y.M. Tzou, Y.H. Lu, G. Sheng, Removal of 3-chlorophenol from water using rice-straw-based carbon, *J. Hazard. Mater.*, vol. 147, 313–318, 2007.
- [4] D. Mohan, K. P. Singh, V. K. Singh, Wastewater treatment using low cost activated carbons derived from agricultural by products—A case study, *J. Hazard. Mater.*, vol.152, 1045–1053, 2008.
- [5] M. Aliabadi, I. Khazaei, M. Hajiabadi, and S. Fazel, Removal of rhodamine B from aqueous solution by almond shell biosorbent, *Journal of Biodiversity and Environmental Sciences*, vol. 2, 39–44, 2012.
- [6] B. K. Singh and N. S. Rawat, Comparative sorption equilibrium studies of toxic phenols on flyash and impregnated flyash, *Journal of Chemical Technology and Biotechnology*, vol. 61, 307–317, 1994.
- [7] D. H. Lataye, I. M. Mishra, and I. D. Mall, Pyridine sorption from aqueous solution by rice husk ash (RHA) and granular activated carbon (GAC): Parametric, kinetic, equilibrium and thermodynamic aspects, *Journal of Hazardous Materials*, vol. 154, 858–870, 2008.
- [8] D. Mohan, K. P. Singh, S. Sinha, and D. Gosh, Removal of pyridine derivatives from aqueous solution by activated carbons developed from agricultural waste materials, *Carbon*, vol. 43, 1680–1693, 2005.
- [9] J. M. Salman, V. O. Njoku, and B. H. Hameed, Adsorption of pesticides from aqueous solution onto banana stalk activated carbon, *Chemical Engineering Journal*, vol. 174, 41–48, 2011.
- [10] I. Bhatti, K. Qureshi, R. A. Kazi, and A. K. Ansari, Preparation and characterization of chemically activated almond shell by optimization of adsorption parameters for removal of chromium (VI) from aqueous solution, *International Journal of Chemical and Biological Engineering*, vol. 1, 149–154, 2008.


- [11] L. M. Cotoruelo, M. D. Marques, J. Rodriguez-Mirasol, J. J. Rodriguez, T. Cordero, Lignin-based activated carbons for adsorption of sodium dodecylbenzene sulfonate: Equilibrium and kinetic studies, *J. Colloid. Interf. Sci.*, vol. 332, 39–45, 2009.
- [12] R. Aravindhan, J. R. Rao, B. U. Nair, Preparation and characterization of activated carbon from marine macro algal-biomass, *J. Hazard. Mater.*, vol. 162, 688–694, 2009.
- [13] A. A. Nunes, A. S. Franca, L. S. Oliveira, Activated carbons from waste biomass: An alternative use for biodiesel production solid residues, *Bioresour. Technol.*, vol. 100, 1786–1792, 2009.
- [14] S. Sumathi, S. Bhatia, K. T. Lee, A. R. Mohamed, Optimization of microporous palm shell activated carbon production for flue gas desulfurization: Experimental and statistical studies, *Bioresour. Technol.*, vol. 100, 1614–1621, 2009.
- [15] S. Kumagai, Y. Noguchi, Y. Kurimoto, K. Takeda, Oil adsorbent produced by the carbonization of rice husks, *Waste Manage.*, vol. 27, 554–561, 2007.
- [16] A. Aygun, S. Yenisoay Karakas, I. Duman, Production of granular activated carbon from fruit stones and nut shells and evaluation of their physical, chemical and adsorption properties, *Micropor. Mesopor. Mater.*, vol. 66, 189–195, 2003.
- [17] M. K. Sheikh, *The Pomegranate*, International Book, Lucknow, India, 2006.
- [18] F. Muradoglu, M. F. Balta, K. Ozrenk, Pomegranate (*Punica granatum L.*) genetic resources from Hakkari, Turkey, *Res. J. Agric. Biol. Sci.*, vol. 2 (6), 520–525, 2006.
- [19] M. Olivares-Marin, C. Fernandez-Gonzalez, A. Macias-Garcia, V. Gomez-Serrano, Preparation of activated carbon from cherry stones by chemical activation with ZnCl<sub>2</sub>, *Appl. Surf. Sci.*, vol. 252, 5967–5971, 2006.
- [20] D. Angin, E. Altintig, T. E. Kose, Influence of process parameters on the surface and chemical properties of activated carbon obtained from biochar by chemical activation, *Bioresour. Technol.*, vol. 148, 542–549, 2013.
- [21] J. M. V. Nabais, P. J. M. Carrott, M. M. L. R. Carrott, J. A. Menendez, Preparation and modification of activated carbon fibres by microwave heating, *Carbon*, vol. 42, 1315–1320, 2004.
- [22] W. Li, L. Zhang, J. Peng, N. Li, X. Zhu, Preparation of high surface area activated carbons from tobacco stems with K<sub>2</sub>CO<sub>3</sub> activation using microwave radiation, *Industrial Crops and Products*, vol. 27, 341–347, 2008.
- [23] H. Deng, L. Yang, G. Tao, J. Dai, Preparation and characterization of activated carbon from cotton stalk by microwave assisted chemical activation- Application in methylene blue adsorption from aqueous solution. *Journal of Hazardous Materials*, vol. 166, 1514–1521, 2009.
- [24] D.A. Jones, T.P. Lelyveld, S.D. Mavrofidis, S.W. Kingman, N.J. Miles, Microwave heating applications in environmental engineering- A review, *Resources, Conservation and Recycling*, vol. 34, 75–90, 2002.



**Nurcan Tugrul** was born in Gaziantep in 1973. Tugrul was graduated from B.Sc., M.Sc. and Ph.D. in Chemical Eng. Department at Yildiz Technical University, Istanbul. Her research interest is in the area of chemical technologies, evaluation of industrial wastes, food drying. She has many articles and studies in international and national conference proceedings and articles.



**Emek Moroydor Derun** was born in Istanbul in 1976. Moroydor Derun graduated from B.Sc. in 1998, M.Sc. in 2000 and Ph. D. in 2005 from Chemical Engineering Department at Yildiz Technical University, Istanbul. Her research interest is in the area of waste management, lightweight concrete, semi conductive materials and boron technology. She has many articles and studies in international and national conference proceedings and articles.



**Sabriye Piskin** graduated from Istanbul Technical University on Chemical Engineering with M.Sc. degree in 1974. She completed a Ph.D. degree at the same department in 1983. Her research interests include boron minerals and compounds, hydrogen storage technologies, fuel cell applications, materials characterization, coal, waste management, corrosion, implants and synthetic materials production. She has more than fifty articles and eighty conference manuscripts pressed at the international area.



**Seyma Nur Turkmen** was completed education as Chemical Engineer at Yildiz Technical University in 2013. She is M. Sc. student at same department of same university. She is working on improvement production methods of the activated carbon from various fruit peels.



**Azmi Seyhun Kipcak** was graduated from Department of Chemical Engineering in Ege University in 2002. After completing the university studies he graduated from Bilgi University from the department of Master of Business Administration in 2004. He worked in Kultur University from 2003 to 2007 as a research assistant then he transferred to Yildiz Technical University at 2008, where he started his M.Sc. studies about Chemical Engineering in 2006. He completed his M.Sc. studies at Yildiz Technical University in 2009 and Ph.D. studies in 2013. Now he is studying on different types of borate synthesis from different raw materials and wastes.