

# Factors Affecting Aluminum Dissolve from Acidified Water Purification Sludge

Wen Po Cheng, Chi Hua Fu, Ping Hung Chen, Ruey Fang Yu

**Abstract**—Recovering resources from water purification sludge (WPS) have been gradually stipulated in environmental protection laws and regulations in many nations. Hence, reusing the WPS is becoming an important topic, and recovering alum from WPS is one of the many practical alternatives. Most previous research efforts have been conducted on studying the amphoteric characteristic of aluminum hydroxide for investigating the optimum pH range to dissolve the Al(III) species from WPS, but it has been lack of reaction kinetics or mechanisms related discussion. Therefore, in this investigation, water purification sludge (WPS) solution was broken by ultrasound to make particle size of reactants smaller, specific surface area larger. According to the reaction kinetics, these phenomena let the dissolved aluminum salt quantity increased and the reaction rate go faster.

**Keywords**—Aluminum, Acidification, Sludge, Recovery.

## I. INTRODUCTION

IN drinking water and wastewater treatment processes, a coagulant, such as aluminum sulfate or poly aluminum chloride may react with colloids/particles in raw water forming settled flocs. After settling the flocs, the resultant chemical sludge is dewatering to produce a sludge cake. In Taiwan, around 120,000 tons of water purification sludge (WPS) is generated from water treatment plants annually, and about 30% of this sludge is alum salt [1], [2]. Alum sludge is composed of the aluminum coagulant and mineral clay in raw water. Water purification sludge contains less heavy metal and organic contamination than wastewater treatment sludge, because the raw water that is used to purify water is relatively clean and the coagulant that is used for treatment is of relatively high quality. Therefore, it is still an issue to choose a disposal method for the water purification sludge (WPS) that would be reasonable in terms of technology and economy. There are laboratory and full scale attempts at using WPS as a component in the manufacture of concrete; as geotechnical works materials; as a potential for use in agriculture; as a primary source of aluminum and iron based coagulants through several recovery process; and for phosphorus reduction during wastewater treatment [3]-[6]. Therefore, recovering aluminum salt from such the large amount of produced water purification sludge is worthwhile.

According to past research, the main approaches for recovering alum from WPS include acidification, basification,

membrane separation, and ion exchange [7]-[14]. Since aluminum hydroxide,  $\text{Al}(\text{OH})_3$ , is an amphoteric compound, it can be dissolved in acid or alkaline solutions. It also reacts with acid to form soluble aluminum ions, and forms soluble  $\text{Al}(\text{OH})_4^-$  ions in alkali. According to [15], if the pH of alum sludge is reduced by adding  $\text{H}_2\text{SO}_4$  to between 1 and 3, then an aluminum recovery rate of approximately 70 to 90% can be achieved. If  $\text{NaOH}$  or  $\text{Ca}(\text{OH})_2$  is used to extract and recover the aluminum, then the aluminum recovery rate is highest at a pH between 11.2 and 11.8. These acidification or basification methods are relatively simple. Therefore, they are commonly used for aluminum recovery and in studies of the regeneration of coagulant. For example, the pH that has recently been found to maximize aluminum dissolution efficiency (in terms of moles of aluminum dissolved per mole of  $\text{H}^+$  or  $\text{OH}^-$  ion) in Taiwan is 2 and 12 in acidification and basification treatments, respectively [16], [17]. However, in the basification process, the humic acid in the alum sludge may easily dissolve in a strong alkaline solution, inhibiting the recovery of the aluminum. Accordingly, the acidification process is generally more convenient and more efficient than the basification process for recovering aluminum from sludge. Additionally, the size of the sludge particles and the dissolution temperature are important factors that influence the dissolution of metal ions. When the sludge particles are small, the ability to form complex bonds between the sludge particles and the metal ions is poor. Such weak bonds may promote the dissolution of the sludge. Therefore, the metal is easily dissolved ( $\text{pH} < 2.5$ ). Additionally, a higher dissolution temperature provides sufficient energy to break the amorphous chemical bonds of the sludge and increase the metal dissolution rate [18], [19]. Accordingly, during the acidification process, increasing the solution temperature may increase the quantity of aluminum dissolved.

## II. EXPERIMENTAL

### A. Sludge Preparation

Sludge was obtained from the sludge drying bed of Ming-Der water treatment plant at Miao-Li, Taiwan. After the sludge was dried at  $60^\circ\text{C}$  and well mixed, a sludge sample was prepared. This water treatment plant uses traditional coagulation and flocculation processes to treat roughly 35,000 tons of water/day. Polyaluminum chloride (basicity, 47.6%;  $\text{Al}_2\text{O}_3$ , 10.57%; Chung Hwa Chemical Industrial Works, Ltd., Taiwan) is added to the rapid-mixing tank. After mixing, the treated water flows into three flocculation tanks that are connected in series. Flocculation mixing was *via* a mechanical paddle. Following flocculation, the

W. P. Cheng is with the National United University, Miaoli, Taiwan 360, (phone: 886-3-7382278; fax: 886-3-7382278; e-mail: cwp@nuu.edu.tw).

C. H. Fu was with National United University, Miaoli, Taiwan 360. (e-mail: alfa-js@yahoo.com.tw).

P. H. Chen is with the National Taipei University, San Shia District, New Taipei City, Taiwan, (e-mail: kphchentw@yahoo.com.tw).

water is treated consecutively by sedimentation, filtration, and chlorination to meet drinking water standards. The sludge samples were dried at 105°C. An Energy Dispersive Spectrometer (EDS) (Fig. 1) was used to analyze the elemental composition of the sludge. Analysis showed that Si, Al, and Fe were the dominant elements. The sludge sample was also analyzed by X-ray diffraction (XRD) to identify its crystal structure. The sludge is primarily composed of SiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> (Fig. 2). Additionally, the sludge may have also contained some Fe<sub>2</sub>O<sub>3</sub>, KAl<sub>3</sub>Si<sub>3</sub>O<sub>10</sub>(OH)<sub>2</sub> (Muscovite), and (Ca,Na)(Si,Al)<sub>4</sub>O<sub>8</sub> (Labradorite). The EDS and XRD results indicate that aluminum is a major metal in the sludge sample. The total amount of aluminum that can leach out in the acidification process was determined using the standard method by Taiwan's Environmental Protection Administration (NIEA R353.00C; dissolved in nitric acid (1:1)). The quantity of aluminum was 40.03 mg Al/1 g sludge.

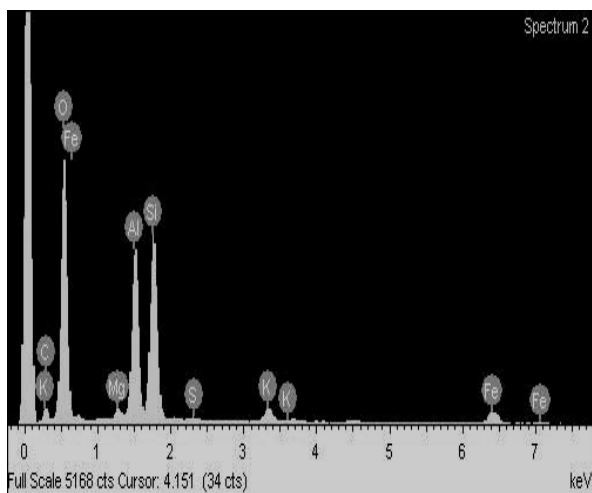


Fig. 1 Element analysis by Energy Dispersive Spectroscopy (EDS)

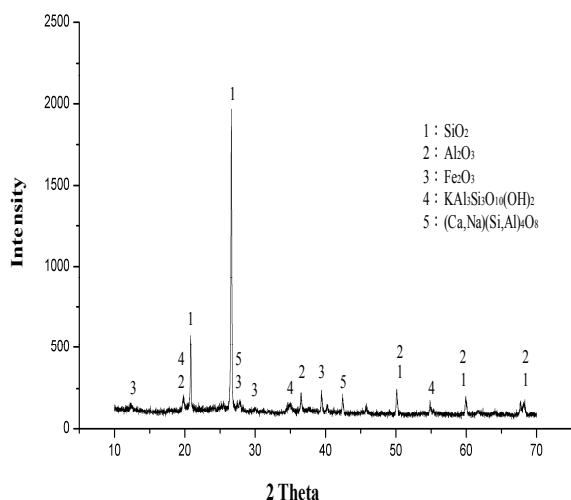


Fig. 2 Crystal structure analysis of the sludge by X-ray diffraction (XRD)

### B. Determination of Acid Dosage

Thirty grams of the sludge sample were added to a beaker with 1000 mL distilled water to prepare 3% (W/W) sludge

solution. Two of these sludge solutions were separately titrated with HCl and H<sub>2</sub>SO<sub>4</sub>. In each titration process, 30 mL of acid was added to the test sludge solution. The pH and added volumes of acids (HCl and H<sub>2</sub>SO<sub>4</sub>) were recorded. If the pH of sludge solution after mixing exceeded two, then another 30 mL acid was added to the solution with mixing until the pH dropped below two, and the total acid dosages were again determined.

### C. Sludge Acidification Experiment

Dried sludge was added to a beaker to prepare 3% (W/W) sludge solution. Then, to two of these sludge solutions was separately added the previously determined volume of H<sub>2</sub>SO<sub>4</sub>. One solution was placement and the other solution mixing with a magnetic stirrer. The effects of acid and reaction time on aluminum recovery were studied. The same 3% (W/W) solution was also treated with ultrasonic waves for one hour. The sample of these ultrasonically treated solutions were added equal volumes of H<sub>2</sub>SO<sub>4</sub>. The solutions with mixing were tested at 25°C, respectively. This experiment demonstrated that the sludge size and reaction temperature influences the dissolution of aluminum. During the reaction, a series of solution samples were filtrated and analyzed by atomic absorption spectrometry (Z-5000 Hitachi Co. Japan) to obtain aluminum concentration.

## III. RESULTS AND DISCUSSION

### A. Determination of Acid Dosage

In this investigation, two acids, H<sub>2</sub>SO<sub>4</sub> and HCl, were used to recover aluminum ions from sludge, and to regenerate aluminum sulfate or aluminum chloride solutions. At 25°C, the different dosages H<sub>2</sub>SO<sub>4</sub> were separately added to each sample of sludge solution.

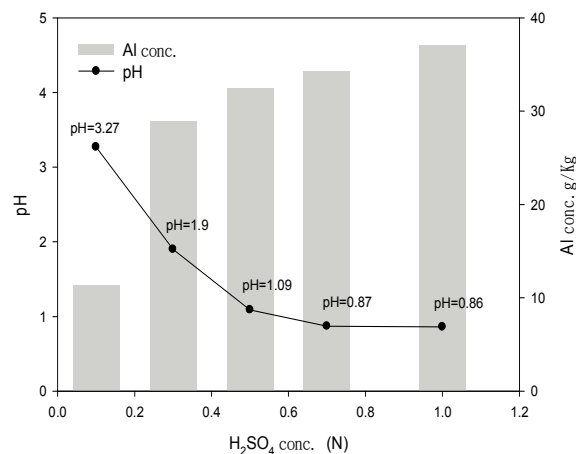


Fig. 3 Relationship between sludge solution pH and dosages of H<sub>2</sub>SO<sub>4</sub>

The pH was recorded as the acid was added with mixing. No more acid was added when the pH stabilized at less than two. According to Fig. 3, in the initial stage of the addition of acid, the acid reacted with the alkaline carbonate, rapidly reducing the pH. When pH the dropped below three, then the acid initiated the dissolution mechanisms reacting with aluminum and other metal hydroxide compounds in the sludge. In this

stage, the pH dropped slowly. When the pH was close to two, the acid dosage was close to the optimal dosage at which aluminum dissolution efficiency was maximal. The added acid was consumed as it destroyed the amorphous chemical bonds and released the alum ions. Therefore, even increasing the acid dosage did not significantly reduce the pH values. Since the drop in pH is strongly affected by the contents of the sludge, including the percentages of  $\text{CaCO}_3$ , metal hydroxide compounds and aluminum, determining acid dosages by simple calculation based on chemical reaction equations is difficult. When 0.3N  $\text{H}_2\text{SO}_4$  were added, the pHs of the acidified sludge solutions dropped to close to but less than two. Therefore, the solution pH was determined to be about 2.

### B. Acid Species Affects Quantity of Dissolved Aluminum

When the reaction temperature was  $25^\circ\text{C}$ , 30 g sludge was added to 1 L distilled water. To two of the test sludge solutions were separately added HCl and  $\text{H}_2\text{SO}_4$  to control the solution pH at 2. Then the test solutions were then mixed using magnetic stirrers for 120 minutes. During the mixing, water samples were extracted every 30 minutes for aluminum concentration analysis. According to the data in Fig. 4, for a particular acid dosage, the dissolved aluminum concentration in the solution that was acidified using  $\text{H}_2\text{SO}_4$  clearly exceeded that in the solution that was acidified using HCl. When the solution was mixed for ten minutes, the aluminum concentration in the  $\text{H}_2\text{SO}_4$ -acidified solution was 206.4 mg/L. This concentration was 68.7% higher than that the aluminum concentration found in the HCl-acidified solution, which was 122.38 mg/L.

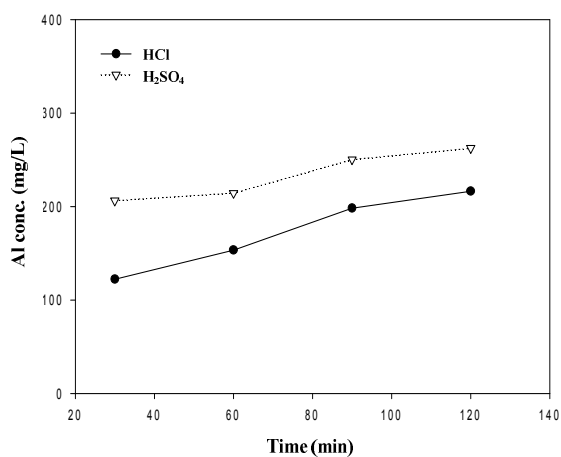


Fig. 4 Relationship between dissolved aluminum concentration and reaction time

When the experiment was terminated at 120 minutes, the aluminum concentration in  $\text{H}_2\text{SO}_4$ -acidified solution was 262.4 mg/L, which was 21.3% higher than the concentration of 216.35 mg/L in the HCl-acidified solution. These results indicate that adding  $\text{H}_2\text{SO}_4$  is more efficient in dissolving aluminum than adding HCl. The main reason is that the chemical affinity between  $\text{SO}_4^{2-}$  and the aluminum ion exceeds that between  $\text{Cl}^-$  and the aluminum ion, and aluminum sulfate complexes are therefore significantly stronger than aluminum chloride

complexes [20], [21]. Accordingly,  $\text{H}_2\text{SO}_4$  relatively easily dissolves the aluminum ions into the solution. Hence,  $\text{H}_2\text{SO}_4$  is traditionally used to recover aluminum from sludge.

### C. Effect of Size of Sludge Particles on Aluminum Dissolution

Three sets of test sludge solutions, formed by adding 30 g sludge to 1 L distilled water, were prepared. These test solutions were treated with placement, stirring and 166 W ultrasonic for two hour.  $\text{H}_2\text{SO}_4$  were separately added to control the solution pH at 2. Then, the solutions of stirring and 166 W ultrasonic pretreatment were mixed using stirrers for 120 minutes at mixing rate 80 rpm. According to Fig. 5, the aluminum concentrations in the ultrasonically treated  $\text{H}_2\text{SO}_4$ -acidified exceed those in the untreated solutions. Additionally the aluminum concentrations in stirring  $\text{H}_2\text{SO}_4$ -acidified solutions exceeded those in the placement-acidified solutions. The aluminum concentration rose rapidly to 345 mg/L for 40 minutes after  $\text{H}_2\text{SO}_4$  was added to the solution (with ultrasonic pretreatment). The dissolution rate increase with increasing reaction time. These results indicate that the dissolution rate can be increased by ultrasonic pretreatment of the acidified solution. The results also indicate that after  $\text{H}_2\text{SO}_4$  was added for 120 minutes, the aluminum concentration in the ultrasonically treated solution was 514 mg/L, which was 1.88 times the concentration (274 mg/L) in the untreated solution. Additionally, if the solution only placement for 120 minutes, the aluminum concentrations in the ultrasonically treated solutions was only 194 mg/L, which was 0.38 times the concentration in the solution of ultrasonic pretreatment. These results indicate that both ultrasonic pretreatment and  $\text{H}_2\text{SO}_4$  acidification can increase the quantity of dissolved aluminum in the test solutions.

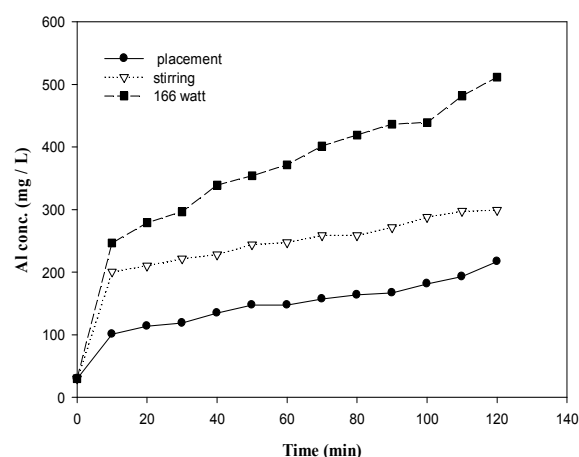


Fig. 5 Effect of ultrasonic pre-treatment on concentrations of dissolved aluminum

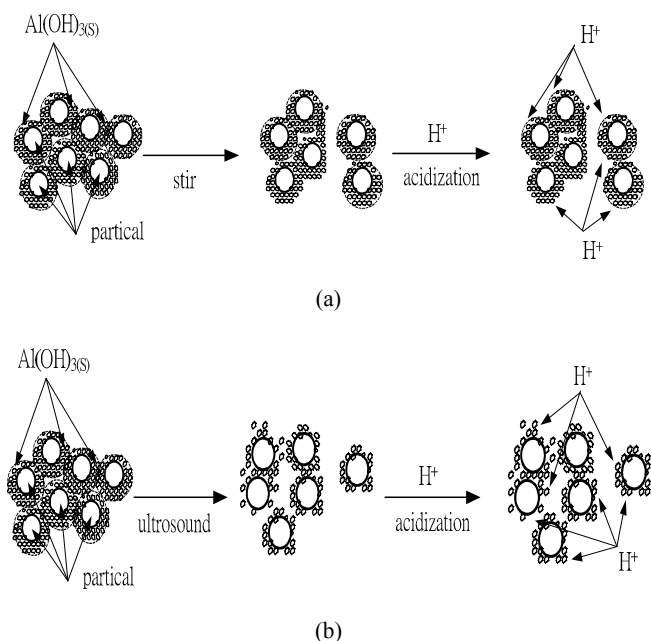


Fig. 6 Alum sludge acidification. (a) Effect of stir mixing on acidified sludge (b) Effect of stir mixing on acidified sludge

During the acidification process, the  $H^+$  ions can react only at the surface of  $Al(OH)_3$  and cannot acidify the interior the  $Al(OH)_3$  particles in the sludge (Fig. 6 (a)). The ultrasonic vibration energy may create erosion points on the surfaces of the particles. Sludge particles vibrated and collided with each other, causing them to break up. Hence, by the capillary effect,  $H^+$  ions may react with the surface and the interior of the  $Al(OH)_3$  during the acidification process (Fig. 6 (b)). Therefore, the  $H^+$  ions in the ultrasonically treated solution have more opportunities to react with the  $Al(OH)_3$  than do those in the untreated solution and more aluminum ions can be dissolved in sludge.

#### IV. CONCLUSION

The acidification method was used in this investigation to recover alum salts from the sludge of a water treatment plant. The effects of acid species and sludge size on aluminum recovery were discussed. Experimental results revealed that ultrasonic treatment could break up the sludge particles and increase the quantity of aluminum dissolved. The aluminum dissolving efficiency in  $H_2SO_4$ -acidified solution exceeded that in  $HCl$ -acidified solution.

#### ACKNOWLEDGMENT

The authors would like to thank Mr. Tun-Jen Tien, Yu-Wei Huang and Ms. Ying-Ju Hsieh for their assistance with the laboratory work. The authors also appreciate the financial support of the National Science Council, Taiwan, R. O. C., (NSC-102-2221-E-239 -001 -MY2).

#### REFERENCES

[1] D.A. Cornwell, R.M. Lemunyon, Feasibility studies on liquid ion exchange for alum recovery from water treatment plant sludges. *J.*

AWWA, 72(1) (1980), pp. 64-68.  
 [2] Q. Imran, M. A. Hanif, M. S. Riaz, S. Noureen, T. M. Ansari, H. N. Bhatti, coagulation/flocculation of tannery wastewater using immobilized chemical coagulants. *Journal of Applied Research and Technology*. 10(2) (2012), pp. 79-86.  
 [3] A.M. Evuti, M. Lawal, Recovery of coagulants from water works sludge: A review. *Advances in Applied Science Research*, 2(2011) , pp. 410-417.  
 [4] A.K. Sengupta P. Prakash, Alum recovery from water treatment works sludges, *Water* 21, 6(1) (2004), pp. 15-16.  
 [5] B. Jimenez, M. Martinez, M. Vaca, Alum recovery and wastewater sludge stabilization with sulfuric acid, *Water Sci Technol*. 56(8) (2007), pp. 133-141.  
 [6] L. Yang, J. Wei, Y. Zhang, J. Wang, D. Wang, Reuse of acid coagulant-recovered drinking water works sludge residual to remove phosphorus from wastewater, *Applied Surface Science*, (305) (2014), pp. 337-346.  
 [7] A.O. Babatunde, Y. Q. Zhao, Constructive approaches toward water treatment works sludge management: an international review of beneficial reuses. *Journal of Critical Reviews in Environmental Science and Technology*, 37(2) (2007), pp. 129-164.  
 [8] T. Yu, D.G. Shen, C.N. Yang, Q.N. Shao, P.S. Song, L.N. He, W.X. Pan, S.P. Bi, Technical development of Aluminum salt recovery from alum sludge. *Journal of The Administration and Technique of Environmental Monitoring*, 21(2) (2009), pp. 45-52.  
 [9] Z. Liu, S.M. Zhu, Y.H. Li, A new regeneration approach to cation resins with aluminum salts: application of desalination by its mixed bed. *Frontiers of Environmental Science& Engineering in China*, 6(1) (2012), pp. 45-50.  
 [10] M.S.E. Abdo., K.T. Ewida, Y.M. Youssef, Recovery of alum from wasted sludge produced from water treatment plants. *J. Environ. Sci. Heal. A*, 28(6) (1993), pp. 1205-1216.  
 [11] B. Jimenez, M. Martinez, M. Vaca, Alum recovery and wastewater sludge stabilization with sulfuric acid, *Water Sci Technol*. 56(8) (2007), pp. 133-141.  
 [12] M.H. Huang, L.D. Chen, S. Zhou, Characteristics and aluminum reuse of textile sludge incineration residues after acidification, *Journal of Environmental Sciences* 23(12) (2011), pp. 1999-2004.  
 [13] W.P. Cheng, C.H. Fu, R.F. Yu, Dynamics of aluminum leaching from water purification sludge. *J. Hazard. Mater.*, 217-218 (2012), pp. 149-156.  
 [14] L. Yang, Y.X. Han, D.T. Wang, High Efficiency Aluminum Coagulant Recovery from Drinking Water Treatment Plant Sludge by Using Ultrasound Assisted Acidification, *Advanced Materials Research*, 777 (2013), pp. 60-64.  
 [15] T. Panswad, P. Chamnan, Aluminum recovery from industrial aluminum sludge. *Water Supply*, 10(4) (1992), pp.159-166.  
 [16] W.L. Peng, Effect of acidification/alkalization on water treatment plant sludge reduction and dewaterability. Master's thesis, Tankang University, Taiwan R.O.C, 2009.  
 [17] S.H. Huang, J.L. Chen, K.Y. Chiang, H.C. Wu, Effects of acidification on dewaterability and aluminum concentration of alum sludge. *Journal of Separation Science and Technology*, 45(8) (2010), pp.1165-1169.  
 [18] Y.J. Chen, H.Y. Teng, P.S. Wei, Y.C. Dung, Monitoring and analysis of acoustic cavitation behaviors in liquid. *Journal of Advanced Engineering*, 2(3) (2007), pp. 157-161.  
 [19] T.J. Mason, *Ultrasound in Environmental Engineering II* (Ed. Neis, U.), 2002, 35, 1.  
 [20] J. Bien, M. Kowalczyk, T. Kamizela, M. Mrwec, The influence of ultrasonic disintegration aided with chemicals on the efficiency of sewage sludge centrifugation. *Environmental Protection Engineering*, 36(1) (2010), pp. 35-43.  
 [21] M.K. Ridley, D.J. Wesolowski, D.A. Palmer, B. Pascale, R.M. Kettler, Effect of sulfate on the release rate of  $Al^{3+}$  from gibbsite in low-temperature acidic waters. *Journal of Environ. Sci. Technol.*, 31 (1997), pp. 1922-1925.