

# Simulation of Piezoelectric Laminated Smart Structure under Strong Electric Field

Shun-Qi Zhang, Shu-Yang Zhang, Min Chen

**Abstract**—Applying strong electric field on piezoelectric actuators, on one hand very significant electroelastic material nonlinear effects will occur, on the other hand piezo plates and shells may undergo large displacements and rotations. In order to give a precise prediction of piezolaminated smart structures under large electric field, this paper develops a finite element (FE) model accounting for both electroelastic material nonlinearity and geometric nonlinearity with large rotations based on the first order shear deformation (FSOD) hypothesis. The proposed FE model is applied to analyze a piezolaminated semicircular shell structure.

**Keywords**—Smart structures, piezolaminates, material nonlinearity, geometric nonlinearity, strong electric field.

## I. INTRODUCTION

SMART structures are those integrated with smart materials like piezoelectric, shape memory alloys, etc., which have a controlled loop with feedback. They have great potential in the applications of vibration control, acoustic control and health monitoring. In order to obtain high actuation forces, strong electric driving field is one of the economical ways without any modification of structural construction. However, applying strong electric fields on piezo actuators, on one hand electroelastic material nonlinear phenomenon will be introduced to the system, on the other hand thin-walled structures will undergo large displacements and rotations. In such a case, numerical models should include both electroelastic material nonlinearity and geometric nonlinearity.

Regarding the modeling and simulation of piezoelectric smart structures, there are plenty of studies available in the literature developed linear numerical models, see e.g. [1], [2] among many others. Due to the simplified assumptions, linear models are only valid for structures subjected to weak electric fields and undergoing small displacements. The numerical models for piezoelectric structures under strong electric field must take into account the electroelastic material nonlinearity. Nelson [3], Tiersten [4] first proposed nonlinear electroelastic equations for piezoelectric materials. Later, the irreversible piezoelectric nonlinearities were investigated experimentally by Li *et al.* [5], Masys *et al.* [6], and studied numerically by Landis [7], Ma *et al.* [8]. Furthermore, Wang *et al.* [9], Yao *et al.* [10] developed analytical models for cantilevered piezoelectric bimorph and unimorph beams under strong electric field. Kusculuoglu & Royston [11], Kapuria & Yasin developed numerical model for dynamic analysis and active

vibration control of piezoelectric smart structures under strong electric fields.

The above mentioned references considered electroelastic material nonlinearity with geometrically linear. Therefore, piezoelectric materials can be subjected to strong electric fields, with the structures undergoing small displacements and rotations. Concerning piezoelectric structures undergoing large displacements and rotations, but without taking into account the electroelastic material nonlinearity, a lot of papers can be found, e.g. von Kármán type nonlinear model [12], [13], moderate rotation nonlinear model [14], and large rotation nonlinear model [15], [16]. However, applying strong electric fields usually yields large displacements and rotations, which cannot be existing separately. In such a case, Yao *et al.* [17] developed a finite element model with von Kármán type nonlinearity and electroelastic material nonlinearity. Von Kármán nonlinearity is the simplest one including very weak geometric nonlinearity, which is only valid for structures undergoing moderately large displacements and small rotations.

In order to simulate piezoelectric smart structures under strong electric fields with large displacements and rotations, the paper develops a numerical model with both geometric and material nonlinearities for piezoelectric integrated smart structures.

## II. MATHEMATICAL MODELS

### A. Electroelastic Material Nonlinearity

Considering electroelastic material nonlinearity, the constitutive equations of piezoelectric materials are expressed as [4]

$$\sigma_p = c_{pq}\varepsilon_q - e_{mp}E_m - \frac{1}{2}b_{mnp}E_mE_n, \quad (1)$$

$$D_m = e_{mq}\varepsilon_q + g_{mn}E_n + \frac{1}{2}h_{mkn}E_kE_n, \quad (2)$$

where  $p$  and  $q$  represent the numbers 1, 2, 3, 4, 5, and 6, while  $n$ ,  $m$ , and  $k$  take the numbers 1, 2, 3. Assuming that the transverse normal strain is neglected for plates and shells and the electric field is applied only along the thickness direction, one yields  $p, q = 1, 2, 4, 5$  or 6 and  $n = m = k = 3$ . Furthermore,  $\sigma_p$  and  $\varepsilon_q$  denote the components of strain and stress vector,  $E_m$  and  $D_m$  are the components of electric field and electric displacement vector,  $c_{pq}$  represent the components of elastic stiffness matrix.

S.-Q Zhang and S.-Y. Zhang are with the School of Mechanical Engineering, Northwestern Polytechnical University, 710072 Xi'an, P. R. China (e-mail: (shunqi.zhang@hotmail.com, sqzhang@nwpu.edu.cn).

Min Chen is with the Department of Industrial Design, Xian Jiaotong - Liverpool University, 215123 Suzhou, Jiangsu, P. R. China.

The coefficients appeared above can be obtained as

$$c_{11} = \frac{Y_1}{1 - \nu_{12}\nu_{21}}, \quad c_{12} = \frac{\nu_{12}Y_2}{1 - \nu_{12}\nu_{21}}, \quad (3)$$

$$c_{22} = \frac{Y_2}{1 - \nu_{12}\nu_{21}}, \quad c_{44} = \kappa G_{23}, \quad (4)$$

$$c_{55} = \kappa G_{13}, \quad c_{66} = G_{12}, \quad (5)$$

$$e_{31} = d_{31}c_{11} + d_{32}c_{12}, \quad (6)$$

$$e_{32} = d_{31}c_{21} + d_{32}c_{22}, \quad (7)$$

$$b_{331} = \beta_{331}c_{11} + \beta_{332}c_{12}, \quad (8)$$

$$b_{332} = \beta_{331}c_{21} + \beta_{332}c_{22}, \quad (9)$$

$$g_{33} = \epsilon_{33} - d_{31}e_{31} - d_{32}e_{32}, \quad (10)$$

$$h_{333} = \chi_{333} - d_{31}b_{331} - d_{32}b_{332}. \quad (11)$$

Here  $(Y_1, Y_2)$ ,  $(\nu_{12}, \nu_{21})$ ,  $(G_{12}, G_{23}, G_{13})$  and  $\kappa = 5/6$  are respectively the Young's moduli, the Poisson's ratios, the shear moduli, and the shear correction factor;  $(d_{31}, d_{32})$  and  $(\epsilon_{33})$  are the piezoelectric constants and the dielectric constant;  $(\beta_{331}, \beta_{332})$  and  $(\chi_{333})$  denote the nonlinear electroelastic constants and nonlinear electroelastic susceptibility constants.

### B. Geometric Nonlinearity

For plate and shell structures, using the first-order shear deformation hypothesis, one obtains the strain-displacement relations with fully geometric nonlinearity as (the details can be found in [18]-[20] [15], [16])

$$\epsilon_{\alpha\beta} = \overset{0}{\epsilon}_{\alpha\beta} + \Theta^3 \overset{1}{\epsilon}_{\alpha\beta} + (\Theta^3)^2 \overset{2}{\epsilon}_{\alpha\beta}, \quad (12)$$

$$\epsilon_{\alpha 3} = \overset{0}{\epsilon}_{\alpha 3}, \quad (13)$$

with the strain components

$$2\overset{0}{\epsilon}_{\alpha\beta} = \overset{0}{\varphi}_{\alpha\beta} + \overset{0}{\varphi}_{\beta\alpha} + \overset{0}{\varphi}_{3\alpha}\overset{0}{\varphi}_{3\beta} + \overset{0}{\varphi}_{\alpha}^{\delta}\overset{0}{\varphi}_{\delta\beta}, \quad (14)$$

$$2\overset{1}{\epsilon}_{\alpha\beta} = \overset{1}{\varphi}_{\alpha\beta} - b_{\beta}^{\lambda}\overset{0}{\varphi}_{\lambda\alpha} + \overset{1}{\varphi}_{\beta\alpha} - b_{\alpha}^{\delta}\overset{0}{\varphi}_{\delta\beta} \quad (15)$$

$$+ \overset{0}{\varphi}_{3\alpha}\overset{1}{\varphi}_{3\beta} + \overset{1}{\varphi}_{3\alpha}\overset{0}{\varphi}_{3\beta} + \overset{0}{\varphi}_{\alpha}^{\delta}\overset{1}{\varphi}_{\delta\beta} + \overset{1}{\varphi}_{\alpha}^{\delta}\overset{0}{\varphi}_{\delta\beta}, \quad (16)$$

$$2\overset{2}{\epsilon}_{\alpha\beta} = -b_{\beta}^{\lambda}\overset{1}{\varphi}_{\lambda\alpha} - b_{\alpha}^{\delta}\overset{1}{\varphi}_{\delta\beta} + \overset{1}{\varphi}_{3\alpha}\overset{1}{\varphi}_{3\beta} + \overset{1}{\varphi}_{\alpha}^{\delta}\overset{1}{\varphi}_{\delta\beta}, \quad (17)$$

$$2\overset{0}{\epsilon}_{\alpha 3} = \overset{1}{v}_{\alpha} + \overset{0}{\varphi}_{3\alpha} + \overset{0}{\varphi}_{\alpha}^{\delta}\overset{1}{v}_{\delta} + \overset{0}{\varphi}_{3\alpha}\overset{1}{v}_{3}. \quad (18)$$

Here  $\epsilon_{\alpha\beta}$  and  $\epsilon_{\alpha 3}$  represent respectively the in-plane strain components and the stress components. Dropping all terms with underlines yields linear plate/shell theory. Based on the linear theory, containing additionally the squares and products of transverse displacement gradients, one obtains von Kármán type nonlinear plate/shell theory. Including the fully geometrically nonlinear strain-displacement relations and considering finite shell director rotations, one leads to large rotation nonlinear theory.

In the FOSD hypothesis, 5 degrees of freedom at each node are usually considered. The fully geometrically nonlinear strain-displacement relations contain 6 parameters. In order to represent finite rotation of shell director, the 5 degrees of

freedom are expressed by 6 parameters as (see [20])

$$\overset{0}{v}_1 = u, \quad (19)$$

$$\overset{0}{v}_2 = v, \quad (20)$$

$$\overset{0}{v}_3 = w, \quad (21)$$

$$\overset{1}{v}_1 = \sin(\varphi_1) \cos(\varphi_2), \quad (22)$$

$$\overset{1}{v}_2 = \sin(\varphi_2), \quad (23)$$

$$\overset{1}{v}_3 = \cos(\varphi_1) \cos(\varphi_2) - 1. \quad (24)$$

Here  $\overset{0}{v}_i$  and  $\overset{0}{v}_j$  are the 6 parameters in the strain-displacement relations. Moreover,  $u, v, w$  denote the translational displacements,  $\varphi_1$  and  $\varphi_2$  are the rotations. For linear theory and von Kármán type nonlinear theory, small or moderate rotations of the shell director are assumed, resulting in  $\cos \varphi = 1$  and  $\sin \varphi = \varphi$ , which leads to  $\overset{1}{v}_1 = \varphi_1, \overset{1}{v}_2 = \varphi_2$  and  $\overset{1}{v}_3 = 0$ .

### C. Finite Element Model

Using the principle of virtual work yields nonlinear static equilibrium equations and sensor equations with consideration of both geometric and material nonlinearities as

$${}^t\mathbf{K}_{uu}\Delta\mathbf{q} + {}^t\mathbf{K}_{u\phi}\Delta\Phi_a = \mathbf{F}_{ue} - {}^t\mathbf{F}_{ui}, \quad (25)$$

$${}^t\mathbf{K}_{\phi u}\Delta\mathbf{q} + {}^t\mathbf{K}_{\phi\phi}\Delta\Phi_s = \mathbf{G}_{\phi e} - {}^t\mathbf{G}_{\phi i}. \quad (26)$$

Here  $\mathbf{K}_{uu}, \mathbf{K}_{u\phi}, \mathbf{K}_{\phi u}, \mathbf{K}_{\phi\phi}$  represent the stiffness matrix, the piezoelectric coupled stiffness matrix, the coupled capacity matrix and the piezoelectric capacity matrix, respectively;  $\mathbf{F}_{ue}, \mathbf{F}_{ui}, \mathbf{G}_{\phi e}$  and  $\mathbf{G}_{\phi i}$  are, respectively, the external force vector, the in-balance force vector, the external charge vector and the in-balance charge vector;  $\Phi_a$  and  $\Phi_s$  denote, respectively, the actuation voltage vector and the sensor voltage vector.

For clear description, several abbreviations are introduced. The finite element model considers geometric and material linear effects based on the FOSD hypothesis is abbreviated as LIN5WE, in which WE denotes weak electric field. Employing the electroelastic material nonlinearity for strong driving electric field (SE), the FE models considering geometric linear and von Kármán nonlinear theory are respectively shorted as LIN5SE and RVK5SE. Furthermore, the model including large rotation geometric nonlinear theory with material nonlinear relations is denoted by LRT56SE.

## III. NUMERICAL EXAMPLES

In this section, a semicircular cylindrical shell is considered as the numerical example, where two piezoelectric layers are bonded at the inner and outer surfaces, as shown in Fig. 1. The host structure is made of graphite/epoxy (T300/976) stacked as 4 substrate layers  $[45^\circ / -45^\circ]_s$  with equal thickness of 0.254 mm. The piezoelectric layers made of 3203HD has the thickness of 0.254 mm. The material properties of 3203HD and T300/976 are given in Table I.

The semicircular cylindrical shell is subjected to a driving voltage of 254 V on both piezoelectric layers. Calculating the

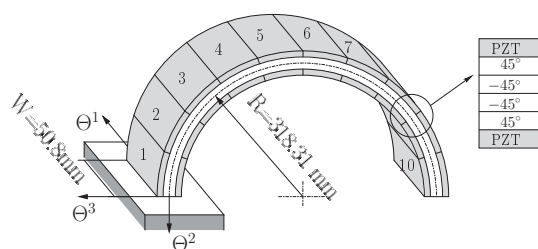


Fig. 1 Clamped piezolaminated semicircular cylindrical shell

TABLE I  
MATERIAL PROPERTIES

Properties	3203HD <sup>a,b</sup>	T300/976
$Y_1$ (GPa)	60.24	150
$Y_2$ (GPa)	60.24	9
$\nu_{12}$	0.253	0.3
$\nu_{23}$	0.494	0.3
$G_{12}$ (GPa)	20.04	7.1
$G_{23}$ (GPa)	19.084	2.5
$G_{13}$ (GPa)	19.084	7.1
$d_{31}$ ( $\times 10^{-12}$ m/V)	-320	/
$d_{32}$ ( $\times 10^{-12}$ m/V)	-320	/
$\epsilon_{33}/\epsilon_0$ <sup>c</sup>	3800	/
$\beta_{331}$ ( $\times 10^{-18}$ m <sup>2</sup> V <sup>-2</sup> )	-520	/
$\beta_{332}$ ( $\times 10^{-18}$ m <sup>2</sup> V <sup>-2</sup> )	-520	/

<sup>a</sup> CTS Corporation [21]

<sup>b</sup> Kapuria & Yasin [22]

<sup>c</sup> Electrical permittivity of air,  $\epsilon_0 = 8.85 \times 10^{-12}$  F/m.

#### IV. CONCLUSION

To simulate piezoelectric smart structures under strong electric fields with large displacements and rotations, the paper has developed a nonlinear FE model for piezolaminated smart structures based on the FOSD hypothesis, in which the electroelastic material nonlinearity and large rotation geometric nonlinearity are taken into account.

The proposed model is applied to analyze a piezolaminated semicircular shell structure. The results show that large discrepancy occurs between the linear and nonlinear predictions. Moreover, in the analysis of the semicircular shell, the RVK5SE curve is very close to LIN5SE, but both of them are different from LRT56SE curve, which indicates that von Kármán type nonlinearity is too weak to predict behavior precisely.

#### ACKNOWLEDGMENT

The work is supported by the National Natural Science Foundation of China (Grant No. 11602193), the State Key Laboratory of Structural Analysis for Industrial Equipment, Dalian University of Technology - China (Grant No. GZ15212), and the State Key Laboratory of Mechanics and Control of Mechanical Structures, Nanjing University of Aeronautics and astronautics - China (Grant No. MCMS-0517G01).

#### REFERENCES

- [1] J. S. Moita, P. G. Martins, C. M. M. Soares, and C. A. M. Soares, "Optimal dynamic control of laminated adaptive structures using a higher order model and a genetic algorithm," *Computers and Structures*, vol. 86, pp. 198–206, 2008.
- [2] S.-Q. Zhang, R. Schmidt, P. C. Müller, and X.-S. Qin, "Disturbance rejection control for vibration suppression of smart beams and plates under a high frequency excitation," *Journal of Sound and Vibration*, vol. 353, pp. 19–37, 2015.
- [3] D. F. Nelson, "Theory of nonlinear electroacoustics of dielectric, piezoelectric, and pyroelectric crystals," *The Journal of the Acoustical Society of America*, vol. 63, no. 6, pp. 1738–1748, 1978.
- [4] H. F. Tiersten, "Electroelastic interactions and the piezoelectric equations," *The Journal of the Acoustical Society of America*, vol. 70, no. 6, pp. 1567–1576, 1981.
- [5] S. Li, W. Cao, and L. E. Cross, "The extrinsic nature of nonlinear behavior observed in lead zirconate titanate ferroelectric ceramic," *Journal of Applied Physics*, vol. 69, no. 10, pp. 7219–7224, 1991.
- [6] A. J. Masys, W. Ren, G. Yang, and B. K. Mukherjee, "Piezoelectric strain in lead zirconate titanate ceramics as a function of electric field, frequency, and dc bias," *Journal of Applied Physics*, vol. 94, no. 2, pp. 1155–1162, 2003.
- [7] C. M. Landis, "Non-linear constitutive modeling of ferroelectrics," *Current Opinion in Solid State and Materials Science*, vol. 8, pp. 59–69, 2004.
- [8] L. Ma, Y. Shen, J. Li, H. Zheng, and T. Zou, "Modeling hysteresis for piezoelectric actuators," *Journal of Intelligent Material Systems and Structures*, vol. 27, no. 10, pp. 1404–1411, 2016.
- [9] Q.-M. Wang, Q. Zhang, B. Xu, R. Liu, and L. E. Cross, "Nonlinear piezoelectric behavior of ceramic bending mode actuators under strong electric fields," *Journal of Applied Physics*, vol. 86, no. 6, pp. 3352–3360, 1999.
- [10] L. Q. Yao, J. G. Zhang, L. Lu, and M. O. Lai, "Nonlinear dynamic characteristics of piezoelectric bending actuators under strong applied electric," *Journal of Microelectromechanical Systems*, vol. 13, no. 4, pp. 645–652, 2004.
- [11] Z. K. Kusculuoglu and T. J. Royston, "Nonlinear modeling of composite plates with piezoceramic layers using finite element analysis," *Journal of Sound and Vibration*, vol. 315, pp. 911–926, 2008.

hoop and radial displacements, one obtains the deformed shape of the central line by using different models, as presented in Fig. 2.

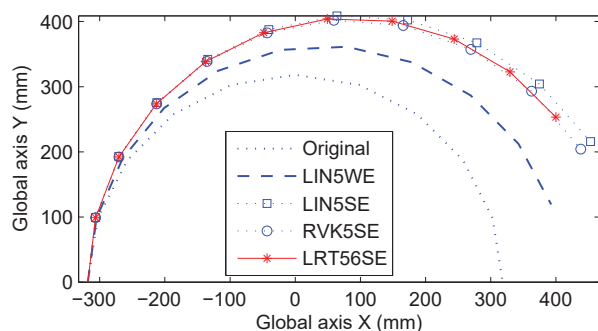


Fig. 2 Central line deformation of the semicircular shell

The numerical results are respectively using linear theory (LIN5WE), geometrically linear with material nonlinear (LIN5SE), von Kármán type nonlinear with material nonlinear (RVK5SE), and large rotation geometrically nonlinear with material nonlinear (LRT56SE). The results show that the linear prediction is far different from the nonlinear predictions. LIN5SE and RVK5SE curves are quite similar, but has relatively large discrepancy compared with LRT56SE result. This is because von Kármán type nonlinear theory is the simplest one, which includes very weak geometric nonlinearity. However, the nonlinear model LRT56SE considers fully geometric nonlinearity with large rotation, as well as the electroelastic material nonlinearity.

- [12] S. Panda and M. C. Ray, "Nonlinear finite element analysis of functionally graded plates integrated with patches of piezoelectric fiber reinforced composite," *Finite Elements in Analysis and Design*, vol. 44, pp. 493–504, 2008.
- [13] R. Schmidt and T. D. Vu, "Nonlinear dynamic FE simulation of smart piezolaminated structures based on first- and third-order transverse shear deformation theory," *Advanced Materials Research*, vol. 79 - 82, pp. 1313–1316, 2009.
- [14] S. Lentzen, P. Klosowski, and R. Schmidt, "Geometrically nonlinear finite element simulation of smart piezolaminated plates and shells," *Smart Materials and Structures*, vol. 16, pp. 2265–2274, 2007.
- [15] S. Q. Zhang and R. Schmidt, "Large rotation FE transient analysis of piezolaminated thin-walled smart structures," *Smart Materials and Structures*, vol. 22, p. 105025, 2013.
- [16] S. Zhang and R. Schmidt, "Static and dynamic FE analysis of piezoelectric integrated thin-walled composite structures with large rotations," *Composite Structures*, vol. 112, pp. 345–357, 2014.
- [17] L. Q. Yao, J. G. Zhang, L. Lu, and M. O. Lai, "Nonlinear extension and bending of piezoelectric laminated plate under large applied field actuation," *Smart Materials and Structures*, vol. 13, pp. 404–414, 2004.
- [18] L. M. Habip, "Theory of elastic shells in the reference state," *Ingenieur-Archiv*, vol. 34, pp. 228–237, 1965.
- [19] L. Librescu, *Elastostatics and Kinetics of Anisotropic and Heterogeneous Shell-Type Structures*. Leyden: Noordhoff International, 1975.
- [20] I. Kreja and R. Schmidt, "Large rotations in first-order shear deformation FE analysis of laminated shells," *International Journal of Non-Linear Mechanics*, vol. 41, pp. 101–123, 2006.
- [21] *CTS Corporation*: <http://www.ctscorp.com/> (accessed on 17/02/1017).
- [22] S. Kapuria and M. Y. Yasin, "A nonlinear efficient layerwise finite element model for smart piezolaminated composites under strong applied electric field," *Smart Materials and Structures*, vol. 22, p. 055021, 2013.

**Shun-Qi Zhang** is an associate professor at the School of Mechanical Engineering, Northwestern Polytechnical University, China. He received the B.S. and M.S. degrees in mechanical engineering from Northwestern Polytechnical University, China, in 2007 and 2010, respectively, and then obtained the Ph.D. degree from RWTH Aachen University, Germany, in 2014. His main research interests are structural mechanics, smart structures, composite structures, computational solid mechanics, and active vibration control.