

# The Effect of the Reaction Time on the Microwave Synthesis of Magnesium Borates from $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ , $\text{MgO}$ and $\text{H}_3\text{BO}_3$

E. Moroydor Derun, P. Gurses, M. Yildirim, A. S. Kipcak, T. Ibroška, S. Piskin

**Abstract**—Due to their strong mechanical and thermal properties magnesium borates have a wide usage area such as ceramic industry, detergent production, friction reducing additive and grease production. In this study, microwave synthesis of magnesium borates from  $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$  (Magnesium chloride hexahydrate),  $\text{MgO}$  (Magnesium oxide) and  $\text{H}_3\text{BO}_3$  (Boric acid) for different reaction times is researched. X-ray Diffraction (XRD) and Fourier Transform Infrared (FT-IR) Spectroscopy are used to find out how the reaction time sways on the products. The superficial properties are investigated with Scanning Electron Microscopy (SEM). According to XRD analysis, the synthesized compounds are 00-041-1407 pdf coded Shabinite ( $\text{Mg}_5(\text{BO}_3)_4\text{Cl}_2(\text{OH})_{5,4}(\text{H}_2\text{O})$ ) and 01-073-2158 pdf coded Karlite ( $\text{Mg}_7(\text{BO}_3)_3(\text{OH},\text{Cl})_5$ ).

**Keywords**—Magnesium borate, microwave synthesis, XRD, SEM.

## I. INTRODUCTION

**B**ORATES are significant compounds because of their properties of lightweight, mechanical resistance, low thermal expansion temperature [1]. As a subgroup of borates magnesium borates are noticeable materials owing to their thermal and mechanical endurance, high coefficient of elasticity [2]-[4]. Magnesium borates are used as thermo luminescence materials, corrosion and friction reducing additive, hydrocarbon production catalysts, a matrix for ferro-elastic materials [4]-[10]. They also have an important potential to be a radiation shielding material.

The main production ways of magnesium borates are solid-state and hydrothermal method. In hydrothermal method, the synthesized the compounds are hydrated on the other hand, in thermal method the products are dehydrated.

Several methods of magnesium borate synthesis have been reported up to the present. Agaogulları et al. synthesized different compounds such as  $\text{MgB}_4\text{O}_7$ ,  $\text{Mg}_2\text{B}_2\text{O}_5$  and  $\text{Mg}_3\text{B}_2\text{O}_6$  by mechanical annealing [5]. Zhihong and Mancheng used hydrothermal method to produce  $2\text{MgO} \cdot \text{B}_2\text{O}_3 \cdot \text{H}_2\text{O}$  from  $\text{MgO}$  and  $\text{H}_3\text{BO}_3$  [11]. Li et al. synthesized  $\text{Mg}_2\text{B}_2\text{O}_5$  nanorods by mechanical treatment and sintering methods [1]. Karakassides

et al. used sol-gel route to manufacture magnesium borate compounds [12]. Li et al. used chemical vapor deposition method to produce  $\text{Mg}_2\text{B}_2\text{O}_5$  compound [13].

Microwave-assisted synthesis of magnesium borates is a solid-state method in which boron and magnesium sources are mixed homogeneously and reacted in a microwave furnace [14]. In literature there are a few studies about microwave synthesis of magnesium borates. Ay et al. used  $\text{MgNO}_3$ ,  $\text{B}_2\text{O}_3$  and  $\text{H}_3\text{BO}_3$  as raw materials to produce magnesium borates at 750W microwave power and a reaction time of 10 minutes. However, the products were amorphous for different molar ratios of starting materials [15]. Guler et al. reacted  $\text{MgO}$  and  $\text{H}_3\text{BO}_3$  in a microwave furnace at 700 W during 10 minutes of reaction time, but similarly with Ay [15] the products were amorphous [16]. Kipcak et al. used reactants of  $\text{MgO}$  and  $\text{H}_3\text{BO}_3$  for microwave synthesis of magnesium borates at different microwave powers and magnesium borate hydrate minerals were produced at the reaction conditions of 270W- 8 minutes and 360W-3minutes.

In the present study, the impact of reaction time on microwave synthesis of magnesium borate compounds is investigated. The purpose of the study is to produce magnesium borates at shorter reaction times than literature. The starting materials were chosen as  $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ ,  $\text{MgO}$  and  $\text{H}_3\text{BO}_3$ . X-ray Diffraction (XRD), Fourier Transform Infrared (FT-IR) Spectroscopy analyses were applied to the products of different reaction times (between 15 and 240 seconds). The surface structures of synthesized compounds were examined by Scanning Electron Microscopy (SEM).

## II. EXPERIMENTAL

### A. Preparation of Raw Materials

To synthesize magnesium borates by microwave method  $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$  (Magnesium chloride hexahydrate),  $\text{MgO}$  (Magnesium oxide) and  $\text{H}_3\text{BO}_3$  (Boric acid) were selected as starting materials.  $\text{H}_3\text{BO}_3$  was procured from Boron Management Plant in Bandırma, Turkey and ground with agate mortar before usage.  $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$  and  $\text{MgO}$  were supplied from Merck Chemicals and used without any pre-treatment.

### B. Synthesis of Magnesium Borates via Microwave Method

In microwave synthesis of magnesium borates the molar ratio of raw materials was determined as 1:1:8 ( $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ :  $\text{MgO}$ :  $\text{H}_3\text{BO}_3$ ). The starting materials were in the form of

E. Moroydor Derun, P. Gurses, M. Yildirim, T. Ibroška, and S. Piskin are with the Yildiz Technical University, Department of Chemical Engineering, Davutpasa Campus, 34210 Esenler, Istanbul, Turkey (e-mail: moroydor@yildiz.edu.tr, pelingurses@gmail.com, meraly@yildiz.edu.tr, tubaibroska@gmail.com, piskin@yildiz.edu.tr, respectively).

A. S. Kipcak is with the Yildiz Technical University, Department of Chemical Engineering, Davutpasa Campus, 34210 Esenler, Istanbul, Turkey (phone: 0090-212-3834751; fax: 0090-212-3834725; e-mail: skipcak@yildiz.edu.tr, seyhunkipcak@gmail.com).

powder so they were mixed homogeneous and pelletized by Manfredi brand OL57 model press equipment under a pressure of 100 bars to get a closer connection of materials (Fig. 1).



Fig. 1 Manfredi brand OL57 model press equipment



Fig. 2 The prepared pellets

Pellets were put in the microwave furnace with the microwave power of 360W. The reaction times were adjusted as 15, 30, 45, 60, 90, 120, 180, 240 seconds. After reactions the pellets were ground and the products were obtained in powder form.



Fig. 3 Prepared pellets in microwave furnace

### C. Characterization Studies of Raw Materials and Synthesized Compounds

With the object of identify the raw materials and produced magnesium borates X-Ray Diffraction (XRD), Fourier Transform Infrared (FT-IR) Spectroscopy techniques were used. Philips Panalytical XRD instrument was used with Cu- $K\alpha$  tube and the parameters of 45 kV and 40mA. In FT-IR analyses Attenuation Total Reflection (ATR) apparatus was used with scan number of 4, resolution of  $4\text{cm}^{-1}$  and scan range of  $1800\text{cm}^{-1}$ – $650\text{cm}^{-1}$ . Also, the surface texture of both raw materials and products were scrutinized by CamScan

Apollo 300 Field-Emission Scanning Electron Microscopy (SEM) and the chosen detector was Back Scattering Electron (BEI).

## III. RESULTS AND DISCUSSIONS

### A. Characterization Results of Raw Materials

XRD patterns and results of raw materials are given in Fig. 4 and Table I respectively. The raw materials found as Bischofite ( $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ ), Periclase ( $\text{MgO}$ ) and Sassolite ( $\text{H}_3\text{BO}_3$ ) with powder diffraction file (pdf) numbers of 01-077-1268, 01-077-2179 and 01-073-2158, respectively.

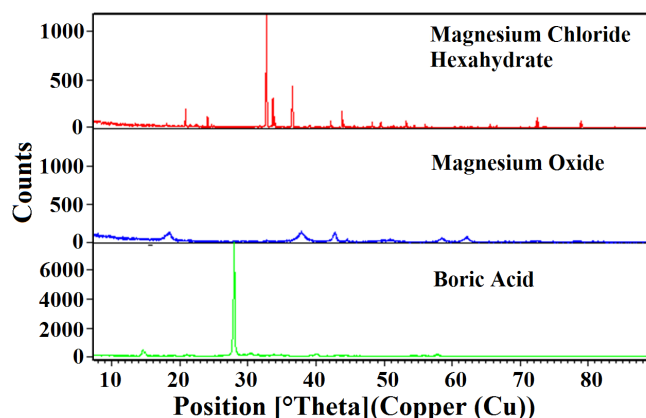


Fig. 4 XRD patterns of raw materials

FT-IR spectra of  $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ ,  $\text{MgO}$ ,  $\text{H}_3\text{BO}_3$  are given in Fig. 5. The raw materials are in rapport with FT-IR ATR inorganic library.

TABLE I  
 XRD RESULTS OF RAW MATERIALS

Pdf code	Raw Material	Mineral Name	Mineral Formula
01-077-1268	Magnesium chloride hexahydrate	Bischofite	$\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$
01-077-2179	Magnesium oxide	Periclase	$\text{MgO}$
01-073-2158	Boric acid	Sassolite	$\text{H}_3\text{BO}_3$

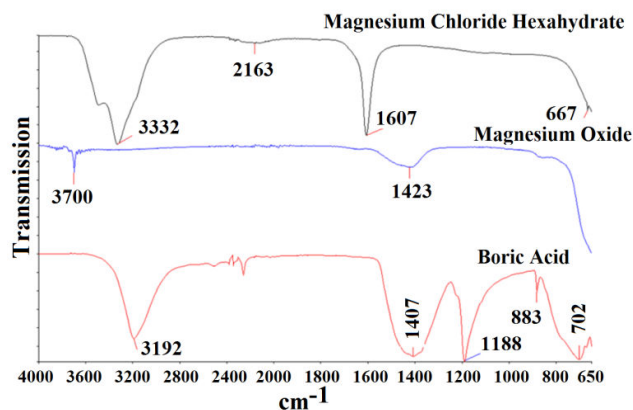


Fig. 5 FT-IR spectra of raw materials

### B. Characterization Results of Raw Materials

XRD patterns and results of synthesized magnesium borates for different reaction times are shown in Fig. 6 and Table II,

respectively.

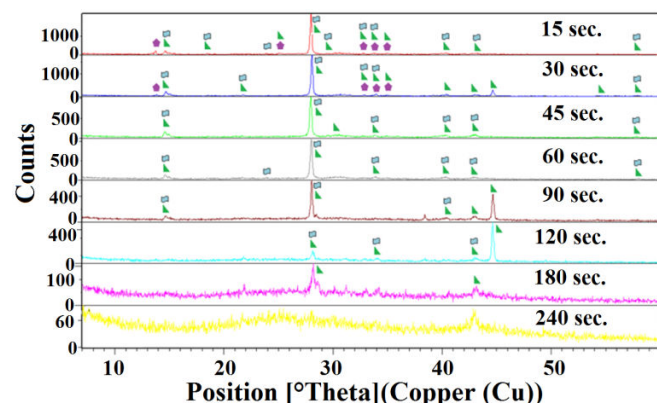


Fig. 6 XRD patterns of synthesized magnesium borate minerals

According to XRD results of products it is seen that with increasing reaction time the product structure turns to amorphous form. For a reaction time of 15 seconds, the crystal structures of synthesized magnesium borate minerals are at the highest level. Both in reactions of 15 and 30 seconds two different types of magnesium borates of Shabynite and Karlite are produced. Up to the reaction time of 120 seconds the formation of crystalline Shabynite is continued. At the reaction times of 180 and 240 seconds the products do not consist crystal phases of magnesium borates.

TABLE II  
XRD RESULTS OF SYNTHESIZED MINERALS

Time (second)	Symbol	Pdf code	Mineral Name	Mineral Formula
15		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
		01-073-2158	Sassolite	$H_3BO_3$
30		00-036-0381	Karlite	$Mg_7(BO)_3(OH,Cl)_5$
		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
45		01-073-2158	Sassolite	$H_3BO_3$
		00-036-0381	Karlite	$Mg_7(BO)_3(OH,Cl)_5$
60		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
		01-073-2158	Sassolite	$H_3BO_3$
90		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
		01-073-2158	Sassolite	$H_3BO_3$
120		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
		01-073-2158	Sassolite	$H_3BO_3$
180		01-073-2158	Sassolite	$H_3BO_3$
		01-073-2158	Sassolite	$H_3BO_3$
240	-	-	-	-

Also, for all reactions the excess boric acid content is observed from XRD results. Therefore, the products of the reaction time of 15 seconds, which has the best results are washed with 96% ethanol to eliminate the excess boric acid. The XRD patterns and results of washed product of the reaction time of 15 seconds are shown in Fig. 7 and Table III.

According to XRD results of washed magnesium borate minerals the synthesized minerals are Shabynite ( $Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$ ) with pdf code of 00-041-1407 and Karlite ( $Mg_7(BO)_3(OH,Cl)_5$ ) with pdf code of 00-036-0381. Also, it is seen from the Fig. 4, the intension of characteristic peaks of magnesium borates are increased after

the removal of boric acid.

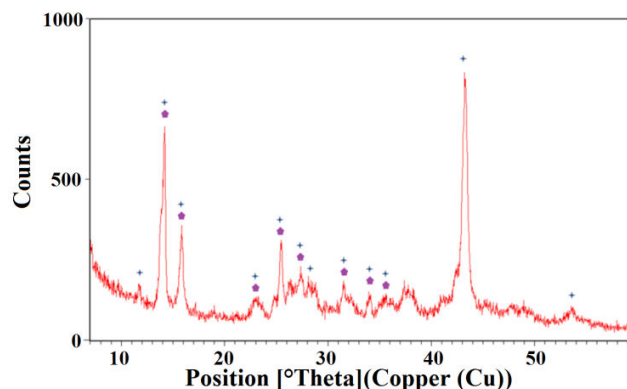


Fig. 7 XRD patterns of washed magnesium borate minerals

TABLE III  
XRD RESULTS OF WASHED PRODUCTS

Time (second)	Symbol	Pdf code	Mineral Name	Mineral Formula
15		00-041-1407	Shabynite	$Mg_5(BO)_3Cl_2(OH)_5 \cdot 4(H_2O)$
		00-036-0381	Karlite	$Mg_7(BO)_3(OH,Cl)_5$

FT-IR spectra of synthesized magnesium borate minerals are shown in Fig. 8. The differences between peaks for every reaction time were minor. According to FT-IR results, the peaks in the ranges of  $1652-1613 \text{ cm}^{-1}$  showed  $\delta(H-O-H)$  bending. The peaks between  $1373-1357 \text{ cm}^{-1}$  corresponded to bending of  $[v_{as}(B_{(3)}-O)]$  and asymmetric stretching of the four coordinate boron  $[v_{as}(B_{(4)}-O)]$  was observed in the ranges of  $1190-996 \text{ cm}^{-1}$ .

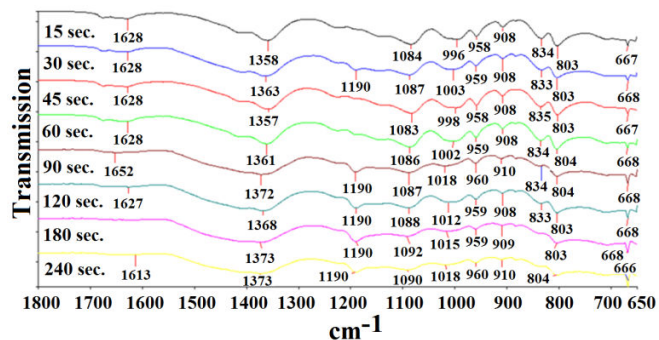


Fig. 8 FT-IR spectra of synthesized magnesium borate minerals

Between the ranges  $960-908 \text{ cm}^{-1}$  symmetric stretching of three coordinate boron  $[v_s(B_{(3)}-O)]$  was beholden. The peaks between  $835-803 \text{ cm}^{-1}$  were coincided with symmetric stretching of the four coordinate boron  $[v_s(B_{(4)}-O)]$ . The peaks around  $667 \text{ cm}^{-1}$  indicated the bending of  $[\delta(B_{(3)}-O)]$ .

The FT-IR results of the synthesized magnesium borates confirm with the literature and show the specific magnesium borate peaks.

The SEM image of synthesized magnesium borate at the reaction time of 15 seconds is given in Fig. 9.

University Scientific Research Projects Coordination  
Department. Project Number: YTU-2013-07-01-YL01.

#### REFERENCES

- [1] L. Shuang, X. Fang, H. Shen, Y. Fan, D. Xu, "A New Route for the Synthesis of  $Mg_2B_2O_5$  Nanorods by Mechano-Chemical and Sintering Process", *Materials Letters*, 2010, 64:151–153.
- [2] X. Tao, X. Li, "Catalyst-Free Synthesis, Structural, and Mechanical Characterization of Twinned  $Mg_2B_2O_5$  Nanowires", *Nano Letters*, 2008, 8: 505-510.
- [3] W. Zhu, G. Li, X. Zhang, L. Xiang, S. Zhu, "Hydrothermal mass production of  $MgBO_2(OH)$  nanowhiskers and subsequent thermal conversion to  $Mg_2B_2O_5$  nanorods for biaxially oriented polypropylene resins reinforcement", *Powder Technology*, 2010, 203:265–271.
- [4] L. Kumari, W. Z. Li, S. Kulkarni, K. H. Wu, W. Chen, C. Wang, C. H. Vannoy, R.M. Leblanc, "Effect of Surfactants on the Structure and Morphology of Magnesium Borate Hydroxide Nanowhiskers Synthesized by Hydrothermal Route", *Nanoscale Res Lett*, 2010, 5:149–157.
- [5] D. Agaogullari, O. Balci, H. Gokce, I. Dursun, M. L. Ovecoglu, "Synthesis of Magnesium Borates by Mechanically Activated Annealing", *Metallurgical and Materials Transactions A*, 2012, 43:2520-2533.
- [6] B. Xu, T. Li, Y. Zhang, Z. Zhang, X. Liu, J. Zhao, "New Synthetic Route and Characterization of Magnesium Borate Nanorods", *Crystal Growth & Design*, 2008, 8:1218–1222.
- [7] W. Zhu, L. Xiang, T. He, S. Zhu, "Hydrothermally Synthesis and Characterization of Magnesium Borate Hydroxide Nanowhiskers", *Chemistry Letters*, 2006, 35:1158-1159.
- [8] J. Zhang, Z. Li, B. Zhang, "Formation and structure of single crystalline magnesium borate ( $Mg_3B_2O_6$ ) nanobelts", *Materials Chemistry and Physics*, 2006, 98: 195–197.
- [9] W. Zhu, X. Zhang, L. Xiang, S. Zhu, "Hydrothermal Formation of the Head-to-Head Coalesced Szaibelyite  $MgBO_2(OH)$  Nanowires", *Nanoscale Res Lett*, 2009, 4:724–731.
- [10] J. Li, F. Wang, Y. Zhang, M. Wang, H. Wang, "Microstructure and Mechanical Properties of Magnesium Matrix Composite Reinforced with Magnesium Borate Whisker", *Journal of Composite Materials*, 2012, 46: 3011–3016.
- [11] L. Zhihong, H. Mancheng, "New Synthetic Method and Thermochemistry of Szaibelyite", *Thermochimica Acta*, 2004, 411:27–29.
- [12] M. A. Karakassides, D. Petridis, G. Mousdis, C. Trapalis, G. Kordas, "Preparation And Infrared Study of Magnesium Borate Gels with a Wide Composition Range", *Journal of Non-Crystalline Solids*, 1996, 202:198-202.
- [13] Y. Li, z. Fan, J. G. Lu, R. Chang, "Synthesis of Magnesium Borate ( $Mg_2B_2O_5$ ) Nanowires by Chemical Vapor Deposition Method", *Chem. Mater.*, 2004, 16, 2512-2514.
- [14] Z. S. Kipcak, E. M. Derun, S. Piskin, "Magnesium Borate Synthesis by Microwave Energy: A New Method", *Journal of Chemistry*, 2013, <http://dx.doi.org/10.1155/2013/329238>.
- [15] E. Ay, "Synthesis and Characterization of Compounds with Some Magnesium Borate Types by Solid-State Reactions", *M.Sc. Thesis*, 2006, Balikesir University, Institute of Science Department of Chemistry.
- [16] H. Guler, F. Kurtulus, E. Ay, G. Celik, I. Doğan, "Solid-State and Microwave-Assisted Synthesis and Characterization of  $Mg_2B_2O_5$  and  $Mg_3(BO_3)_2$ ", *4th International Boron Symposium Proceedings Book*, 2009.

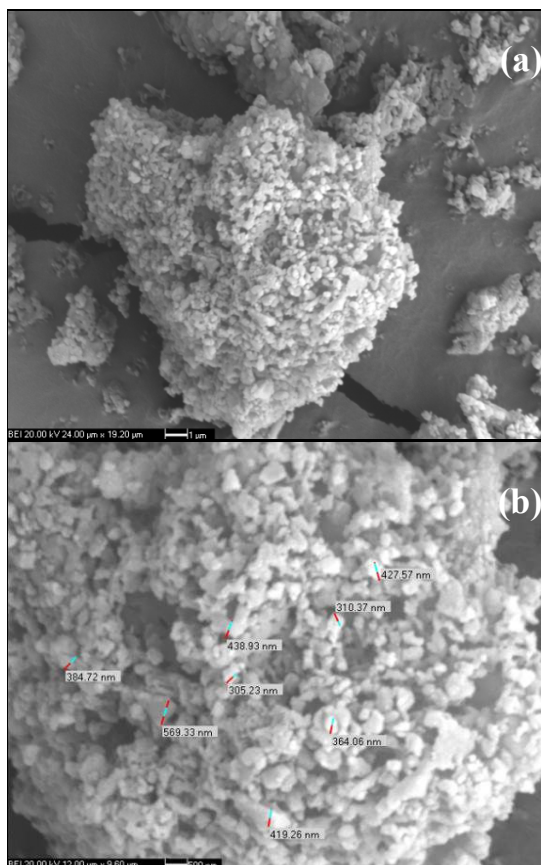


Fig. 9 SEM image of synthesized magnesium borate mineral  
(a) x5000, (b) x10000

According to SEM image, the obtained products are formed of sphere-like crystal aggregates. The magnified image shows that many nano scale particles come together and build up big granular structures. It is observed that the grain diameters of minerals are varied between 570 nm-310 nm.

#### IV. CONCLUSIONS

In this study, it was aimed to produce magnesium borates with  $MgCl_2 \cdot 6H_2O$ ,  $MgO$ ,  $H_3BO_3$  as raw materials via microwave method. Starting out by the purpose of finding out reaction time effects on microwave synthesis of magnesium borates, the operation conditions were chosen as 360W microwave power and 1:1:8 raw material ratios for different reaction times of 15, 30, 45, 60, 90, 120, 180, 240 seconds.

The results of experiments showed that with increasing reaction time the crystallinity of synthesized minerals were decreasing. The best XRD scores were achieved at the reaction time of 15 seconds. For all reaction times the products of experiments were mixture of magnesium borate minerals and boric acid. After washing process of removing excess boric acid obtained products were two magnesium borate minerals of  $Mg_5(BO_3)Cl_2(OH)_5 \cdot 4(H_2O)$  and  $Mg_7(BO_3)3(OH,Cl)_5$ .

#### ACKNOWLEDGMENT

This research has been supported by Yildiz Technical




**Emek Moroydor Derun** was born in İstanbul in 1976. Moroydor Derun was graduated from B.Sc. in 1998, M.Sc. in 2000 and Ph. D. in 2005 from Chemical Engineering Department at Yildiz Technical University, İstanbul. Her research interest is in the areas of waste management, lightweight concrete, semi conductive materials and boron technology. She has many articles and studies in international and national conference proceedings and articles.



**Pelin Gurses** was born in Istanbul in 1988. Gurses graduated B.Sc. in Chemical Eng. Department at Yildiz Technical University, Istanbul, in 2011. She is currently continuing M.Sc. education at the same university. Gurses is interested in synthesis and characterization of magnesium borate minerals and derivatives. She is working as a Product Development

Engineer at Mercedes Benz Turk Bus Plant, as well.



**Meral Yildirim** was born in Diyarbakir in 1989. Yildirim graduated B.Sc. in 2011, M.Sc. in 2013 from Chemical Engineering Department in Yildiz Technical University, Istanbul. She is currently continuing Ph. D. education at the same university. She is interested in synthesis and characterization of borate minerals.




**Azmi Seyhun Kipcak** was graduated from Department of Chemical Engineering in Ege University in 2002. After completing the university studies he graduated from Bilgi University from the department of Master of Business Administration in 2004. He worked in Kultur University from 2003 to 2007 as a research assistant then he

transferred to Yildiz Technical University at 2008, where he started his M.Sc. studies about Chemical Engineering in 2006. He completed his M.Sc. and Ph.D. studies at Yildiz Technical University in 2009 and 2013, respectively. He studied on neutron shielding with boron minerals and the characterization of boron minerals by using XRD, XRF, FT-IR, Raman, DTA/TG, DSC and ICP-OES at the M.Sc. studies and studied on the synthesis of magnesium borates from different raw materials and wastes at the Ph.D. Also he is improving the neutron shielding studies with the synthesized materials and working on the element analysis of Turkish Teas and Coffees. Another research field about the studies he is working is the zinc borate synthesis.



**Tuğba İbroşka** was born in Edirne in 1990. İbroşka graduated B.Sc. in 2012 from Chemical Engineering Department in Yildiz Technical University, Istanbul. She is currently continuing M.Sc. education at the same university. She is interested in synthesis and characterization of non-hydrated borate minerals.



**Sabriye Piskin** graduated from Istanbul Technical University on Chemical Engineering with M.Sc. degree in 1974. She completed a Ph.D. degree at the same department in 1983. Her research interests include boron minerals and compounds, hydrogen storage technologies, fuel cell applications, material characterization, coal, waste management, corrosion, implants and synthetic materials

production.